

2020-07

Cryptogamic packed biofilter as potential adsorbent for CO₂, H₂S and NH₃ impurities from biogas

Temba, Norbert Willibrord

NM-AIST

<https://doi.org/10.58694/20.500.12479/993>

Provided with love from The Nelson Mandela African Institution of Science and Technology

**CRYPTOGAMIC PACKED BIOFILTER AS POTENTIAL ADSORBENT FOR CO₂,
H₂S and NH₃ IMPURITIES FROM BIOGAS**

Norbert Willibrord Temba

**A Dissertation Submitted in Partial Fulfillment of the Requirements for the Degree of
Master's in Sustainable Energy Science and Engineering of the Nelson Mandela African
Institution of Science and Technology**

Arusha, Tanzania

July, 2020

ABSTRACT

The presence of elevated concentrations of carbon dioxide, hydrogen sulfide, ammonia and trace impurities in biogas affect its caloric value as well as causes corrosion and are extremely toxic. There are various methods for removal of these impurities, but most are chemically based, expensive and limited in use. In this work, cryptogams (moss) integrated with soil and biochar packed in a filter have been employed for simultaneous removal of CO₂, H₂S and NH₃, from biogas. Different soil types rich in metallic oxides at a different mass of (100 g, 150 g and 200 g) with a fixed mass of moss and biochar were tested in an on-site experiment to determine the removal efficiency (RE) and sorption capacity (SC). The adsorption dynamics of the filters were investigated at two flow rates, 80 ml/min and 100 ml/min, by determining removal efficiency. For the contribution of each substrate, sorption capacity and breakthrough time were determined by considering 5 g of each substrate that made up the filter. The soils with a high content of extractable cations showed excellent adsorption capacity for H₂S by about 20 g-S/100 g, which was higher than other adsorbents tested. It was found that integrated biofilter made up of bed arrangement of the soil, biochar and moss plant improved the quality of biogas with SC of 11 g-S and RE of 93% for H₂S, 72% for NH₃ and 68% for CO₂.

Keywords: Cryptogams, Biofiltration, Biochar, Removal efficiency, Sorption Capacity.

DECLARATION

I, NORBERT W. TEMBA, do hereby declare to the Senate of the Nelson Mandela African Institution of Science and Technology that this thesis is my own original work and that it has neither been submitted nor concurrently submitted for a degree or similar award in any other institution.

Norbert W. Temba

Name and signature of candidate

Date

The above declaration is confirmed

Prof. Tatiana Pogrebnaya

Name and signature of supervisor 1

Date

Dr. Thomas Kivevele

Name and signature of supervisor 2

Date

COPYRIGHT

This dissertation is copyright material protected under the Berne Convention, the Copyright Act of 1999 and other international and national enactments, in that behalf, on intellectual property. It must not be reproduced by any means, in full or in part, except for short extracts in fair dealing; for researcher private study, critical scholarly review or discourse with an acknowledgment, without written permission of the Deputy Vice-Chancellor for Academic, Research and Innovation, on behalf of both the author and the Nelson Mandela African Institution of Science and Technology.

CERTIFICATION

The undersigned certify that they have read and hereby recommend for acceptance by the Nelson Mandela African Institution of Science and Technology a the dissertation entitled: “Cryptogamic packed biofilter as potential adsorbent for CO₂, H₂S and NH₃ and impurities from biogas” and recommend for examination in partial fulfillment of the requirements for the degree of Masters in Sustainable Energy Science and Engineering of The Nelson Mandela African Institution of Science and Technology.

Principal supervisor

Prof. Tatiana Pogrebnyaya

Signature

Date

Co-supervisor

Dr. Thomas Kivevele

Signature

Date

ACKNOWLEDGMENT

First of all, I am thankful to the almighty God, for granting me strength, good health and life. I wish to express my sincere gratitude to my supervisors; Prof. Tatiana Pogrebnaya and Dr. Thomas Kivevele for their wisdom, advice, assistance, patience, immense knowledge and the highest level of commitment that they have shown to the completion of this dissertation. If not their close supervision, this dissertation would not have been completed. On top of that, I am indebted to the whole community of the NM-AIST for their support during the whole time of my study.

I also extend my sincere thanks to Tanzania Agricultural Research Institute of Tanga, Tanzania for providing the soil profile data from surveyed areas at Kwaraguru Sisal Estate, Kwedzinga. Also special thanks to Mr. Christopher Kellner for allowing to collect raw biogas and conducting purification tests on his biodigesters. Moreover, I would like to expand my grateful appreciation to MESE Department staff who in one way or another provided me with moral support and encouragement; most specifically Prof. Karoli Njau and Prof. Alexander Pogrebnoi to mention a few.

It would not be fair if I will not give sincere thanks to my fellow students of Masters and friends in Materials Energy Science and Engineering (MESE); Mr. Binyoh Theodore, Mr. Clemence Ansbert, Mr. Amos Makoye and PhD students in Materials Science and Engineering (MESE); Mr. Bernard Kivumbi and Mr. Rene Costa.

Finally and exceptionally, my special thanks also go to my family members: My parents Mr. and Mrs. Temba for their support and encouragement as well as my current employer Rural Water Supply and Sanitation Agency, Regional Office - Tanga and my former employer District Executive Director-Pangani Mr. Damian Chambasi for releasing me to pursue my studies. Lastly, may our living God bless you all, amen.

DEDICATION

This work is dedicated to my family, friends and my co-workers who have always been there supporting me throughout every step of the way.

.

TABLE OF CONTENTS

ABSTRACT.....	i
DECLARATION	ii
COPYRIGHT.....	iii
CERTIFICATION	iv
ACKNOWLEDGMENT.....	v
TABLE OF CONTENTS.....	vii
LIST OF TABLES	x
LIST OF FIGURES	xi
LIST OF ABBREVIATIONS AND SYMBOLS	xii
CHAPTER ONE	1
INTRODUCTION	1
1.1 Background of the Problem	1
1.2 Statement of the Problem.....	4
1.3 Rationale of the Study.....	5
1.4 Objectives	5
1.4.1 General Objective	5
1.4.2 Specific Objectives	5
1.5 Research Questions.....	5
1.6 Significance of the Study	6
1.7 Delineation of the Study	6

CHAPTER TWO	7
LITERATURE REVIEW	7
2.1 Biogas Composition.....	7
2.2 Gas Utilization	9
2.3 Working Principle of Air Biofilter.....	11
2.4 Introduction to Cryptogams	12
2.5 The Efficiency of Cryptogams and Soil Biofilter in Biogas Purification.....	13
2.6 Absorption of Sulfides by Oxides.....	15
2.7 Absorption of CO ₂ and H ₂ S by Biochar	16
2.8 Performance Analysis of Other Purification Methods.....	18
2.9 Biofiltration Design and Operating Parameters.....	21
2.9.1 Temperature.....	21
2.9.2 Moisture Content	22
2.9.3 pH Condition.....	22
2.9.4 Nutrient Supply.....	22
2.9.5 Pressure Drop	22
CHAPTER THREE	24
MATERIALS AND METHODS.....	24
3.1 Equipment and Accessories.....	24
3.2 Sample Collection and Preparation.....	24
3.3 Filter Preparation	25

3.4	System Operation.....	27
3.5	Filter Performance Parameters.....	29
	CHAPTER FOUR.....	30
	RESULTS AND DISCUSSION	30
4.1	Soil Type Effect on Biogas Purification	30
4.2	Effect of Varying Soil Mass on Removal Efficiency	32
4.3	Effect of Biogas Flow Rate on the Biofilter T3 Removal Efficiency.....	34
4.4	Analysis of the Function of each Substrate.....	37
	CHAPTER FIVE	43
	CONCLUSION AND RECOMMENDATIONS	43
5.1	Conclusion	43
5.2	Recommendations.....	43
	REFERENCES	45
	APPENDICES	59
	RESEARCH OUTPUT	63

LIST OF TABLES

Table 1:	Composition of biogas, depending on the feedstock.....	7
Table 2:	Requirement to remove gaseous components depending on the biogas utilization (Petersson <i>et al.</i> , 2009).....	9
Table 3:	Trace element concentration ($\mu\text{g g}^{-1}$) in mosses and lichens studied from relatively unpolluted areas in Italy (Adamo <i>et al.</i> , 2003).....	13
Table 4:	Adsorption capacity of biochar during simultaneous and single-gas presentation (Sethupathi <i>et al.</i> , 2017).....	18
Table 5:	Advantages and disadvantages techniques for biogas purification.....	19
Table 6:	Soil database and profile information.....	25
Table 7:	Domestic biodigesters used for the analysis.....	27
Table 8:	Soil types performance in biogas purification, RE, average over operating time ($Q = 80 \text{ ml/min}$).....	31
Table 9:	Effect of soil mass and biogas flow rate on the biofilter T3 performance; H_2S removal efficiencies are given as average values over 2 hours operating time...36	
Table 10:	Summary of BT, SC ($\text{g-S}/100\text{g}$ of sorbent) for all substrates.....	39
Table 11.	Absorption properties of the cryptogamic filter compared to other biofilters.....	40

LIST OF FIGURES

Figure 1:	Cryptogamic cover in different environment	3
Figure 2:	Wobbe index and relative density as a function of CH ₄ content (Hagen <i>et al.</i> , 2001)	8
Figure 3:	Amount of sulfur adsorbed after dosing S ₂ to Al ₂ O ₃ , ZnO, Cu ₂ O and Cu _{0.8} /ZnO at ~300 K (Rodriguez <i>et al.</i> , 1998).....	16
Figure 4:	Preparation of the biofilter.....	26
Figure 5:	Schematic diagram of substrates arrangement in the filter	26
Figure 6:	Photo and schematic diagram of the experimental setup	28
Figure 7:	Biogas purification by filters with different soil samples: RE versus operating time. Test conditions: Q = 80 ml/min, m = 100g, T = 19°C, C ₀ = 36.4% for CO ₂ , 13 ppm for NH ₃ , 836 ppm for H ₂ S	31
Figure 8:	Soil mass effect of the filter T3. Test conditions: Q = 100 ml/min, m ₁ = 100 g, m ₂ = 150 g, m ₃ = 200 g P = 10 kPa C ₀ = 37.5% for CO ₂ , 13 ppm for NH ₃ , 836 ppm for H ₂ S	33
Figure 9:	RE of the filter T3–100 at two different flow rates (80 and 100 ml/min). Test conditions: Q ₁ = 80 ml/min, Q ₂ = 100 ml/min m = 100 g, P = 10 kPa, C ₀ = 37.7% for CO ₂ , 12 ppm for NH ₃ , 915 ppm for H ₂ S	35
Figure 10:	Sulfur removal by various adsorbents: (a) Breakthrough curves, (b) H ₂ S absorption over breakthrough time and (c) Sorption capacities. Test conditions: Q = 100 ml/min, m = 5 g, C ₀ = 307-819 ppm for H ₂ S, Time = 80 min	38
Figure 11:	Adsorption of CO ₂ and NH ₃ by moss substrate in 60 min operation time	39

LIST OF ABBREVIATIONS AND SYMBOLS

AD	Anaerobic Digestion
VOC	Volatile Organic Compounds/gases
RE	Removal Efficiency
SC	Sorption Capacity
BT	Breakthrough Time
C_i	Initial Concentration
C_f	Final Concentration
CDM	Clean Development Mechanism arrangement
UN	United Nations
REDDs	Reducing Emissions from Deforestation and Degradation
RB	Rhodamine B
AC	Activated Carbon
CHP	Combined Heat and Power Engines
APC	Air Pollution Control
SOC	Soil Organic Carbon
VSA	Vacuum Swing Adsorption
CEC	Cation Exchange Capacity
Raw gas	Untreated Biogas

CHAPTER ONE

INTRODUCTION

1.1 Background of the Problem

The increase in energy demands due to population growth, depletion of worldwide oil reserves and the problem of harmful emissions emanating from fossil fuel have put pressure on the world's countries to use renewable energy. One of the renewable energy sources is biogas. It provides the more reliable option of a sustainable form of energy as it is derived from energy crops, agricultural wastes, agro-industrial wastes, municipal waste, etc (Longdong *et al.*, 2014). Biogas production from anaerobic digestion of lignocellulosic biomass in the form of wood residues and agricultural wastes has been attracting wide attention due to their accessibility and environmental sustainability of these materials (Mulat *et al.*, 2018). The gas is mainly composed of methane (CH₄) and carbon dioxide (CO₂) with smaller amounts of hydrogen (H₂S), ammonia (NH₃). In most cases trace amounts of hydrogen sulfide (H₂), saturated or halogenated carbohydrates, nitrogen (N₂) and oxygen (O₂) can be found in the biogas (Persson *et al.*, 2006). Typical raw biogas consists of about 55–65% methane, 30–45% carbon dioxide, traces of hydrogen sulfide, fractions of water vapors and other contaminant gases (Kapdi *et al.*, 2005). Biogas has the potential to counteract many health and environmental impacts connected with other forms of traditional biomass energy. Apart from supplying energy and fertilizer, biogas can also be used as an alternative for the mitigation of greenhouse gas emissions and reduction of global warming.

Biogas produced from digesters is used mainly for cooking and rarely for heating, lighting and electricity generation, simply because of the presence of hydrogen sulfide and other impurities, which together leads to corrosion of metal components in engines and gas burners (Abatzoglou *et al.*, 2009). For biogas to be utilized effectively, purification is required to improve its efficiency and caloric value. Current technologies to purify biogas by removing H₂S, CO₂ and NH₃ use chemical liquids, membrane separation, biological filters, or activated carbon, which are not only costly and cumbersome to use but also result in low removal efficiencies (Ryckebosch *et al.*, 2011).

According to the Kyoto protocol on emissions reduction projects for developing countries, biogas is singled out as a potential renewable energy replacement for kerosene in rural areas in the Clean Development Mechanism arrangement (CDM). Further emphasis by the United

Nations (UN) program of Reducing Emissions from Deforestation and Degradation (REDDs), acts as a recommended initiative for developing countries to reduce emissions and invest in low carbon alternatives such as biogas (Smith *et al.*, 2011).

Soil is the topmost layer of the earth's surface which supports life and primarily made up of a mixture of plants and organic remains, as a result of in situ weathering of rock materials or the accumulation of mineral matter transported by water, wind, or ice. It acts as media for plant growth comprised of organic and inorganic materials by providing physical support, water and nutrients (Nortcliff *et al.*, 2000). Soil differs by its composition and structure. The presence of microbial activities as part of the soil has been studied to account for its usefulness and consider some of the future potential and limitations of its use as a method of air purification for both environmental applications and in the context of bio regenerative life support systems (Nelson *et al.*, 2011). The use of biofilters can improve indoor air pollution, outdoor air emissions of toxic gases thus aiding to reduce the global warming impact of methane (biogas). Also the presence of iron oxide (Fe_2O_3) rich material is a simple, efficient method to remove H_2S in biogas since iron oxide readily reacts with H_2S to form iron sulfide (Fe_2S_3) when biogas passes through it (Zicari, 2003).

Soils rich in metallic oxides are found to be effective in the removal of H_2S (Abatzoglou *et al.*, 2009). A process of soil biofiltration is based on the using of a bed of materials set up such that perforated pipes can deliver the discharge air as it passes through a series of moist, aerated biological material where the gas is absorbed and dissolved in soil solution (Nelson *et al.*, 2011). Soil biofiltration is considered among the best available technology and more fool-proof operation, because of lower investment and operating costs; they are suitable where the pollutant loading is in low concentration or low volume discharge (Leson *et al.*, 1991). Primarily, they have been used for the control of foul odors and reduction in potentially toxic trace gases. The design employs either soil medium or compost in a system that makes use of natural soil processes for dissolution, adsorption and microbial metabolism of inorganic gases and volatile organics present in the effluent air (Nelson *et al.*, 2011).

Another component that has been investigated for air biofiltration is biochar. It can be defined as a black carbon-rich material made up from the decomposition of plant-derived organic matter (waste biomass) in a low or zero oxygen environmental (i.e. pyrolysis or gasification) to release abundant energy gases which are used for power generation or production of liquid fuels (Ahmad *et al.*, 2014; Manyà, 2012). In another more descriptive definition biochar is the

carbonaceous solid product made from the thermochemical conversion of organic material in an oxygen-depleted environment (Shackley *et al.*, 2012). Biochar research has shown considerable key findings in carbon sequestration, agronomics, greenhouse gas emissions, soil quality, soil acidity, soil salinity and soil fertility (Lehmann *et al.*, 2003; Van Zwieten *et al.*, 2010).

Furthermore, studies by Agegnehu *et al.* (2016) and Schulz *et al.* (2013) showed improvements in soil physicochemical properties including soil organic carbon (SOC) and cation exchange capacity (CEC) by using co-composited biochar as well as biochar-composite mixes in soil modifications.



Figure 1: Cryptogamic cover in different environment

Furthermore, it is known to be an efficient and cost-effective sorbent for different kinds of pollutant removal. Biochar contains unmodified activated carbon which mechanically removes sulfur from active sites by deposition in the presence of water which slows down the degeneration process (Primavera *et al.*, 1998). For example, straw-based biochar was identified as a cost-effective substitute for activated carbon for its adsorptive ability towards dye removal in wastewater (Qiu *et al.*, 2009). The results showed biochar was slightly more effective than AC to adsorb RB (rhodamine B) due to the RB–Biochar electrostatic interactions and RB protonation at low pH.

Cryptogamic covers are photoautotrophic communities, consisting of cyanobacteria, algae, fungi, lichens and bryophytes, that is, liverworts and mosses in variable proportions (Lenhart *et al.*, 2015). These communities can provide food webs by photosynthesis and nitrogen

fixation, which is particularly important in arid regions and other terrestrial environments with a low abundance of organic nutrients. Cryptogams are estimated to be responsible for almost half of the total terrestrial biological nitrogen fixation of $\approx 49 \cdot 10^9 \text{ kg year}^{-1}$ and carbon uptake of $\approx 3.9 \cdot 10^9 \text{ ton year}^{-1}$ which amounts to $\approx 7\%$ of the net primary production of terrestrial vegetation (Elbert *et al.*, 2012). Example of cryptogams are as shown in Fig. 1.

Lichens and mosses are cryptogamic organisms that exist in almost all terrestrial ecosystems and by virtue of their ability to tolerate long periods of drought may even colonize areas with extreme environmental conditions. Because of their high surface: volume ratio, the simple anatomy and absence of a cuticle they accumulate heavy metals and concentrating them in their tissues (Adamo *et al.*, 2003). These organisms are also considered to be effective in recording relative spatial and temporal deposition patterns of contaminants due to their characteristics in accumulating and retaining a variety of contaminants. Integrating plants and soil biofiltration for the elimination of technogenic and volatile organic gases (VOC) has been studied to provide means of biological purification without the use of consumables (Nelson *et al.*, 1994; Wolverton *et al.*, 1984). Incorporating different media in packed bed filter has shown successful results in biofiltration for a wide range of air pollutants and VOCs (Dumont, 2015; Nelson *et al.*, 2011; Yoon *et al.*, 2002). Natural organic medium primarily composed of compost, peat, leaves, wood bark and soil has been studied for the removal of toluene contaminated air and VOCs (Sorral *et al.*, 1997; Yoon *et al.*, 2002). This study aimed to apply the properties of cryptogams integrated with soil and biochar packed in a filter to simultaneously remove CO_2 , H_2S and NH_3 from biogas.

1.2 Statement of the Problem

Significant biogas yields have already been achieved from the various feedstocks; however, the quality of the gas produced has been a great challenge. The presence of CO_2 and H_2S significantly reduces the fuel value and performance of biogas in both domestic and industrial applications. Therefore, proposing inexpensive and environmentally friendly methods of purification by eliminating unwanted gases, for example, CO_2 , H_2S and NH_3 , could enable easy compression for transportation, reduce toxic emissions and finally add value to the biogas. Carbon dioxide present in the biogas composition accounts for increased corrosiveness of engines and storage facilities, toxicity in animals and plants and lowers efficiency and calorific value of the fuel. The combustion of H_2S results in the release of sulfur dioxide (SO_x), which is a greenhouse gas. The H_2S is an inorganic acid that attacks the surface of metals when they

are placed in direct contact (Gosh, 2007). Furthermore, NH_3 insignificant concentrations cause complications for gas engines and during combustion emitted gases (NO_x) are often limited by manufacturers. Studies show that combustion of ammonia leads to the formation of nitrous oxide (NO_x) which is very poisonous to both plants and animals (Persson *et al.*, 2006).

The present technology used in biogas purification includes; membranes, chemical and biological scrubbing which are very expensive require substantial energy inputs and produce chemically harmful byproducts. Also, the chemicals used are corrosive and hence require safety precautions both in design and operations. This study aims at using the properties of moss integrated with iron-rich soil to provide an inexpensive and effective filter that uses minimum energy to operate.

1.3 Rationale of the Study

All gases produced from the biodigester, only methane is combustible, carbon dioxide, hydrogen sulfide and ammonia reduce the fuel efficiency of the biogas and therefore need to be removed or significantly reduced to the very minimum. By purifying the produced biogas, it will enable the fulfillment of needed requirements and standardization for gas appliances, easy transportation to various locations and as a result, leads to increase heating value for domestic and industrial applications.

1.4 Objectives

1.4.1 General Objective

To fabricate a prototype of a cryptogamic integrated biofilter for the adsorption of carbon dioxide, hydrogen sulfide and ammonia from biogas.

1.4.2 Specific Objectives

- (i) To analyze soil composition and physicochemical properties.
- (ii) To determine effective moss-soil optimal composition for biofiltration process.
- (iii) To assess the effect of varying experimental parameters on the performance efficiency of biofilter.

1.5 Research Questions

- (i) What is the soil organic matter and iron oxide composition of soil samples?

- (ii) What is optimal moss- soil filters for effective removal of CO₂, H₂S and NH₃ from biogas?
- (iii) What are the optimum experimental conditions of the filters for active biogas purification?

1.6 Significance of the Study

According to the fact that of all gases produced from the biodigester, only methane is combustible, carbon dioxide and hydrogen sulfide reduce the fuel calorific value hence its efficiency. Removal of these impurities from biogas will improve its usage and in turn reducing environmental pollution.

1.7 Delineation of the Study

The study was conducted experimentally on a domestic biogas digester. The biofilter was fabricated at the Laboratory using the components (substrates) involving soil, biochar and cryptogams (moss) in variable proportion, to investigate its performance in biogas purification. The parameters that were varied include mass, soil type and flow rate. The results were used to extrapolate the removal efficiency and sorption capacity of each component to determine its practicability and sustainability.

CHAPTER TWO

LITERATURE REVIEW

2.1 Biogas Composition

The main composition of biogas typically ranges 50 to 65% CH₄, 30 to 45% CO₂, traces of H₂S, NH₃ and moisture. For example, in literature, it is reported the CH₄ is the main component of biogas in a range between 40 and 70% and lower heating value between 15 to 30 MJ/Nm³ (Tippayawong *et al.*, 2010). The exact composition depends on the type of feedstock used and anaerobic conditions. Table 1 presents typical biogas composition, which depends on the feedstock used. Feedstock refers to any substrate that can be converted to methane by anaerobic bacteria (Steffen *et al.*, 1998).

Table 1: Composition of biogas, depending on the feedstock

Gas	Units	Organic Waste	Sewage	Landfill
Methane	% vol	60 – 70	55 – 65	45 – 55
Carbon dioxide	% vol	30 – 40	35 – 45	30 – 40
Nitrogen	% vol	<1	<1	5 – 15
Hydrogen Sulfide	ppm _v	10 – 2000	10 – 40	50 – 300

Rasi *et al.* (2007)

The biogas produced from organic waste on a farm varies depending on the feed stream. Biogas produced from the cow slurry contains 55-75% CH₄, 70-80% CH₄ from pig slurry, 60-80% CH₄ from chicken slurry and 70-80% CH₄ from food slurry (Steffen *et al.*, 1998). As observed organic wastes produce the high H₂S content. Biogas also contains other compounds in trace amounts such as halogenated compounds, siloxanes and aromatic compounds. Water vapor is also present in biogas as a product of anaerobic digestion process and may also contain some dust particles (Pettersson *et al.*, 2009).

Untreated or raw biogas is normally saturated with water and absolute water quantity depends on the temperature of the biodigester. It has been studied by Ryckebosch *et al.* (2011), that at 35°C the water content is approximately 5%. However, it should be removed before use for most energy applications. The levels of H₂S has been reported to in some cases to be in a range of 0-0.4% v/v of total biogas (Kuria *et al.*, 2008). This gas is corrosive on metallic appliances

such as copper, steel, iron and lead pipes and gas holders if not removed from the biogas (Horikawa *et al.*, 2004). The concentration of H₂S above this level should be removed from the biogas before use as reported by Tippayawong *et al.* (2010). When biogas is burned SO₂/SO₃ is emitted which is even more dangerous and poisonous than H₂S itself. During combustion NH₃ and halogenated hydrocarbons produce harmful and corrosive products, which can immensely damage engines and pipelines (Persson *et al.*, 2006). Upgrading biogas to natural gas quality is also a critical multi-step procedure. After removal of water (vapor), H₂S, trace compounds of siloxanes and NH₃, the removal of CO₂ is essential to obtain the quantity that meets the Wobbe index. According to Hagen *et al.* (2001) the Wobbe index is an indicator of the quality of a fuel gas, measured from heat produced by burning through a defined orifice under standard temperature and pressure conditions. If the Wobbe index of the natural gas is higher than the minimum limit, the mixture of natural gas and upgraded gas can meet the pipeline specification for the national gas grid. Upgrading biogas by removing CO₂, lowers the relative density and increases the calorific value and thus increasing the Wobbe index, as shown in Fig. 2.

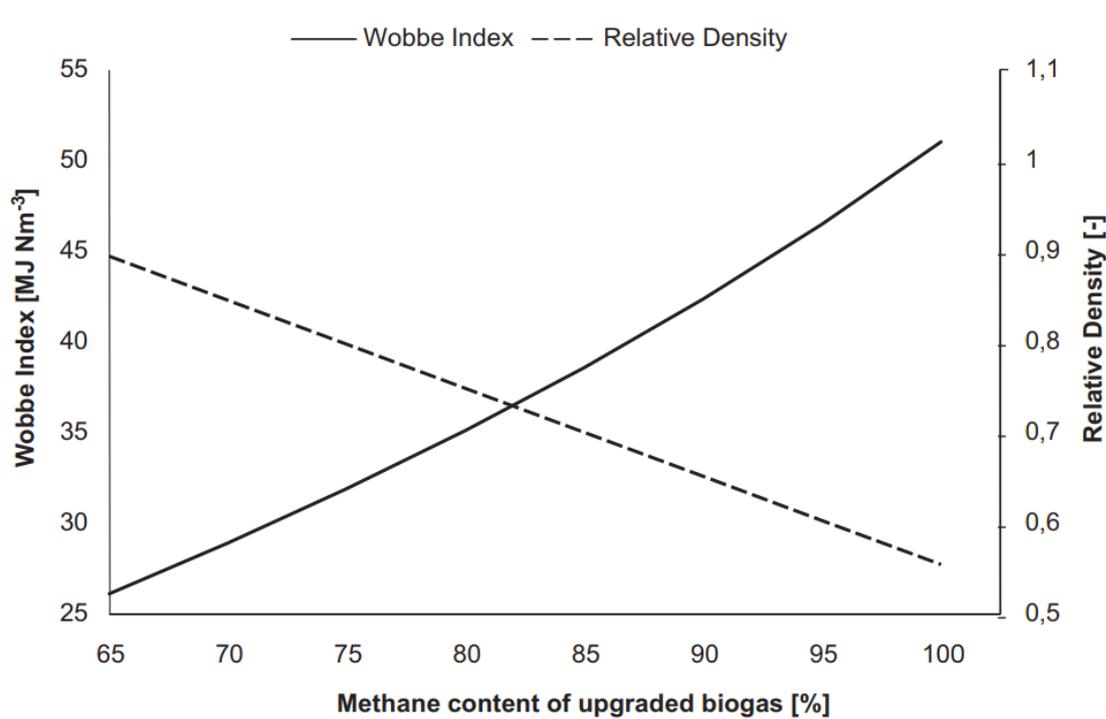


Figure 2: Wobbe index and relative density as a function of CH₄ content (Hagen *et al.*, 2001)

Carbon dioxide removal at an industrial scale is nowadays achieved by physical/chemical technologies based on their high degree of success and commercial availability. These removal

methods a) Pressure Swing Adsorption, b) Vacuum Swing Adsorption (VSA), c) Membrane separation, d) Cryogenic separation and e) Biological removal.

2.2 Gas Utilization

As a renewable fuel, biogas can be used for various applications designed for natural gas. However, not all gas appliances require the same gas standards. There is a significant difference between daily requirements for stationary biogas applications and fuel gas or pipeline quality. Boilers, Gas engines, diesel engines and all other combined heat and power engines (CHP engines) have different standards for gas quality to be used. As shown in Table 2, unwanted gaseous components need to be removed depending on the biogas utilization.

Table 2: Requirement to remove gaseous components depending on the biogas utilization (Petersson *et al.*, 2009)

Application	H ₂ S	CO ₂	H ₂ O
Gas heater (boiler)	< 1000 ppm	no	no
Kitchen stove	yes	no	no
Stationary engine (CHP)	< 1000 ppm	no	no condensation
Vehicle fuel	yes	recommended	yes
Natural gas grid	yes	yes	yes

In fuel application for vehicles, raw biogas cannot be used as it affects engine performance; SO₂ and SO₃ formed during the combustion of H₂S, which are more toxic and causes corrosion as a result it brings about maintenance concerns. Besides, NH₃ causes the formation of NO_x, when dissolved in water becomes corrosive and leads to an increase in antiknock properties of engines. By upgrading the gas, it aids to the following advantage a) high calorific value, b) constant gas quality, c) less corrosion caused by high levels of H₂S and NH₃, d) less clogging due to high water content. The upgraded biogas is called biomethane, a product equivalent to natural gas with 96 – 98.5% methane (Bauer *et al.*, 2013). The calorific value of biogas is between 20 – 28 MJ/m³ depending on the CH₄ content meanwhile that of liquefies pressurize gas LPG is 36 MJ/m³ (Salum *et al.*, 2009).

Quality of biomethane is an important criterion for a particular application for example (transnational) to be fed into the gas grid and the end-use applications. Compared to conventional fuels, the level of standardization is sparse for gaseous fuels. The international

ISO (International Organization for standardization) issued a natural gas standard, ISO 13686:1998 "Natural gas - Quality designation" and a standard for compressed natural gas, ISO 15403 Natural gas – Natural gas for use as a compressed fuel for vehicles (Thrän *et al.*, 2014). This standard is essential based on its application specifically for natural gas grids and vehicle fuel as shown in Table 2. According to Krich *et al.* (2005) there are about three steps to upgrading biogas to biomethane, which are; removal of H₂S, removal of moisture and removal of CO₂. Some of the methods used for H₂S removal involve:

- (i) Air injected into the biodigester
- (ii) Reaction with iron oxide or hydroxide (iron sponge)
- (iii) Use of activated-carbon sieve
- (iv) Water scrubbing
- (v) Biological removal on a filter bed / Biological desulphurization

According to Pokorna *et al.* (2015) biological desulphurization is the addition of air into the storage tank which at the same time serving as the gasholder. It is one of the simplest methods of H₂S removal in the digester as microorganisms (sulfur-oxidizing bacteria) reduce the H₂S concentration by 95% to less than 50 ppm. Elemental sulfur is produced from the oxidation of Hydrogen sulfide, while phototrophic sulfur-oxidizing bacteria reduce CO₂ and incorporates it into organic compounds. The process is considered as chemosynthesis since the bacteria do not release oxygen to the atmosphere as shown in Eq. (2.1) below:



Some other industrial methods that have been applied to eliminate CO₂ and H₂S from raw biogas are:

- (i) Pressure swing adsorption
- (ii) Water scrubbing
- (iii) Chemical scrubbing with amines
- (iv) Membrane separation
- (v) Cryogenic separation

In addition to H₂S and CO₂, removal of trace impurities notably phosphorus compounds, allows biogas to be used in the production of hydrogen for fuel cells (Cebula, 2009). Chemical absorption of CO₂ and H₂S by aqueous solutions in a packed column was also investigated by (Tippayawong *et al.*, 2010). The aqueous solutions employed were sodium hydroxide, calcium hydroxide and mono-ethanolamine. The results revealed that over 90% removal efficiency by aqueous solution with CO₂ and H₂S was removed below the detection limit, thus creating CH₄ enriched fuel. Therefore, removal of multiple impurities in the biogas is useful in raising its high value.

2.3 Working Principle of Air Biofilter

Biofiltration refers to the process air pollution control (APC) technology in which off-gases containing biodegradable volatile organic compounds (VOC) or inorganic air toxins are vented through a biologically active material (Leson *et al.*, 1991). This process employs biomonitors, bio accumulators and bioindicators in filtering air impurities using naturally occurring plants (Mosses, Lichens and Liverworts) and inorganic materials. Application of lichens and mosses as biomonitors of air pollution has been studied since these organisms rely on atmospheric sources for nutrients and in addition to that, they do not shed plant parts as readily as vascular plants. Among the characteristic features of these organisms is to accumulate and retain a range of contaminants. As a result, they are very useful in recording relative spatial and temporal deposition patterns of contaminants (Nash III *et al.*, 1988).

In a survey to assess the contribution of thermal springs and fumaroles to environmental levels of selected trace elements employing lichens and mosses to be used as bio accumulators suggested that lichens and mosses can be preferred as accumulators of As, Cd, Cu, Mo and S deposition. Concentration differences between lichens and mosses were statistically significant for Al, B, Fe, Hg, Pb, Sb and Zn, with mosses retaining higher values than lichens except for Hg and Zn (Loppi *et al.*, 2000). They have also shown high tolerance of ammonia uptake and nitrogen fixation up to the annual average of 0.001 mgm⁻³, which is the critical level for annual average NH₃ concentrations for sensitive ecosystems (i.e. those in which lichens and bryophytes are important components) (Cape *et al.*, 2009).

Removal of NH₃ is essential to increase the calorific value of biogas. In most cases, NH₃ is mostly formed during degradation of proteins and its concentration depends upon the substrate composition and the pH in the digester. To separate ammonia from the mixture of other

impurities the gas has to be dried and upgraded, therefore a separate cleaning step is in most cases not necessary (Pettersson *et al.*, 2009). Alternatively, NH₃ can also be removed from the gas by a washing process with diluted nitric or sulfuric acid. But the use of these acids demands stainless steel installation which can be expensive for small scale applications like biogas cleaning (Ryckebosch *et al.*, 2011). In addition to that, Chung *et al.* (2000) experimented on biotreatment of H₂S and NH₃ containing waste gases by co-immobilized cells biofilter. The biofilter was packed with co-immobilized cells, H₂S and NH₃ gas mixture were continuously supplied at various ratios. The results revealed that the removal efficiency remained above 95% with disregard of the ration of H₂S and NH₃ used.

2.4 Introduction to Cryptogams

The Plants are autotrophic organisms as they can synthesize their food with the help of sunlight and photosynthetic pigments from carbon dioxide and water. They exist in both aquatic and terrestrial habitats. They are of different shapes and sizes. Some plants are microscopic and some grow up to 100 m. Plants are essential in regulating biogeochemical cycles and also in the exchange of gases that support life in our biosphere. Plants can be categorized into two groups namely; cryptogams and phanerogams (Saini, 2010). Cryptogams are made up of flowerless or seedless plants while phanerogams are flowering or seed-bearing plants. Cryptogams are made up of bryophytes, lichens, fungi and algae. Mosses are grouped in bryophytes. Bryophytes tend to diverge from vascular plants especially in influencing cycles of elements, energy and water as a result of their unique physiology and ecology. For example, they can sustain longer periods of water scarcity than vascular plants and can recover quickly with hydration. As a result of a poorly developed conduction system, water and solutes are taken up over the entire plant surface.

The absence of both gametophyte stomata and effective cuticles allows a free exchange of solutions and gases across its cell surface (Turetsky, 2003). The property makes bryophytes effective in trapping water and nutrients. Furthermore, it subjects them to more sensitivity to atmospheric depositions over vascular plants. It has been observed that moss accumulates traces of SO₂ more expeditiously than the leaves of vascular plants (Winner, 1988). Mosses and lichens have been experimented as air pollutant monitors and also biomonitors of trace metals (Adamo *et al.*, 2003). The observations of this by Bargagli *et al.* (2002) and Adamo *et al.* (2003) are as shown in Table 3.

Furthermore, there have been studies to improve the carbon net uptake and nitrogen fixation in different types of ecosystems on a continental and global scale (Elbert *et al.*, 2012). Further studies aimed at analyzing the effectiveness of lichens and mosses in geothermal power plants as biomonitors of trace elements, the result showed both organisms could be used as biomonitors of elements arising from geothermal emissions. However, Bargagli *et al.* (2002) observed that they can't be used conversely in mineral deposits as biomonitors of metals and metallic compounds. In urban areas, where mosses and lichens are scarce, the bags technique has been developed to monitor air pollution.

Table 3: Trace element concentration ($\mu\text{g g}^{-1}$) in mosses and lichens studied from relatively unpolluted areas in Italy (Adamo *et al.*, 2003)


Element	Mosses				Epiphytic lichens	
	<i>Sphagnum capilifolium</i>	<i>Hylocomium splendens</i>	<i>Hypnum cupressiforme</i>	<i>Pseudevernia furfuracea</i>	Foliose (e.g. <i>Parmelia</i> , <i>Hypogymnia</i>)	Fruticose (e.g. <i>Ramalina</i> , <i>Evernia</i>)
Al	118	700	1600	415	n.d	120-150
As	0.11	n.d	n.d	0.15	0.7-2.0	0.3-1.5
Cd	0.38	0.3	0.3	0.46	<0.1-0.3	<0.1-0.2
Co	0.43	n.d	n.d	0.23	<0.1-0.3	<0.1-0.2
Cr	1.60	0.9	2.4	2.23	1-4	<1-3
Cu	5.54	8.6	8.4	5.42	4-10	4-10
Fe	675	457	1290	363	150-300	150-300
Mn	552	150	178	29.9	20-80	20-60
Mo	0.41	n.d	n.d	0.26	<0.1-0.5	<0.1-0.5
Ni	2.35	1.3	1.8	1.81	1-3	<1-2
Pb	18.87	17.0	15	23.0	1-8	1-5
Ti	11.46	n.d	n.d	8.73	5-35	5-20
V	1.55	n.d	n.d	1.49	<1-3	<1-2
Zn	83	32.0	26	99	20-90	20-70

2.5 The Efficiency of Cryptogams and Soil Biofilter in Biogas Purification

Bacteria and fungi have been widely considered in the treatment of a range of environmental pollutants, as degradants which involves the breakdown of organic compounds by either through biotransformation into less complex metabolites or through mineralization to form inorganic minerals, H₂O, O₂ (aerobic) or CH₄ (anaerobic). Fungi have also been investigated concerning their capacity to remove volatile contaminants in air biofilters. The use of fungi and other microorganisms in biofiltration have reached a relatively high elimination capacity and are resistant to low pH values and moisture content (Kennes *et al.*, 2004). In this case, polluted

air flows through a porous matrix that acts as a support for microorganism development. By controlling the humidity of the medium fungi can be enriched over bacteria.

Further studies have also concluded that various species of cryptogams can be used to sight metal deposition of the surrounding the ecosystem quite quickly and at a lower cost. The absence of a well-developed cuticle and roots in mosses and lichens, causes these organisms to rely mainly on atmospheric deposits for nourishment. Also, these organisms do not shed plant parts and they accumulate atmospheric pollutants at higher concentrations than that of vascular plants (Bargagli, 1989; Bargagli *et al.*, 2002; Groet, 1976; Rühling, 1994). Some of the species cryptogams in the form of moss *Hypnum cupressiforme* and the epiphytic lichen *Parmelia caperata* were found to be effective biomonitors of trace metals in the atmosphere (Bargagli *et al.*, 2002). Therefore, these species effectively use fine particles as a means to ensure their survival. As its true nature, under a controlled environment, they can absorb a significant amount of pollutants. This gives room for further research in integrating them with other bio accumulators so they can coexist to perform this particular function. Soil and sand have also shown significant capacity in adsorbing trace elements and gas from the atmosphere. Studies also observed that brown soil in the form of allophonic soil contains iron in the form of hydrated iron (Fe_2O_3) (Dillon, 1990). The iron oxide in these soils would readily react with hydrogen sulfide (H_2S) to form iron sulfide (Fe_2S_3) and water (H_2O) when the gas mixtures passed through the soil filter.



Since elemental sulfur is thought to build upon the surface of sulfide minerals during their oxidation by O_2 as shown in Eqn. 2.3, the ability of acidophilic bacteria to oxidize elemental sulfur using ferric iron as an oxidant is geochemically in the leaching of sulfide ores to form sulphates (Sato, 1960).



Eqn. 2.4 (assuming pH 2) is -75 kcal and the free energy of the reaction Eqn 2.5 (assuming pH 2) is -124 kcalS⁻¹ atom (-247 kcal for the whole reaction), there is more energy available using O₂ than Fe³⁺ as electron acceptor (Brock *et al.*, 1976).

Soil supports the growth of bioindicators (Mosses and Lichens) which filters particulate matter and mineral elements from the atmosphere. The primary source of carbon for moss and lichens is mainly CO₂. The use of soil bio-filtration provides a cheap solution in terms of investment capital and operating energy costs to handle contaminants in moderate concentrations. The soil biofilter can be designed to improve performance and optimize efficiency through handling temperature, pH, moisture content, airflow rates and soil organic matter (Nelson *et al.*, 2011).

2.6 Absorption of Sulfides by Oxides

Many industrial by-products specifically from oil refineries contain H₂S present from coal gas. Broekhuis *et al.* (1992) presented a medium-temperature process for H₂S removal using aqueous metal sulfate solutions. The results were the metal sulfide would oxidize with ferric ion to form sulfur as shown in Eqn. 2.3. Rodriguez *et al.* (1998) investigated the reaction of H₂S and S₂ with metal/oxides surface in relation to band-gap size and chemical reactivity. The theoretical method used was ab initio self-consistent field (SCF) calculations and a simple model that combines perturbation theory with Huckel and tight-binding methods on a series of oxides (Al₂O₃, Cr₂O₃, Cr₃O₄, Cu₂O, ZnO) and metal/oxide (Cu/ Al₂O₃, Cu/ZnO) surfaces.

The results showed that for the adsorption of S₂ on Al₂O₃, Cu₂O and ZnO, the surface chemistry of the molecules on oxides that have a relatively small band-gap is much higher than on alumina. Therefore, the metal and metal oxides of ZnO and Cu₂O are more reactive towards sulfur than sites of alumina (Al₂O₃) as shown in Fig. 2.

Also, wood chips impregnated with iron oxide have been experimented to selectively adsorb H₂S and mercaptans. The reaction of Iron oxides and sulfur leads to the formation of insoluble iron sulfides. Additionally, it's possible to prolong the bed life by admitting air, which leads to the formation of elemental sulfur and regenerating the iron oxide. The media will need to be replaced once it becomes clogged with elemental sulfur.

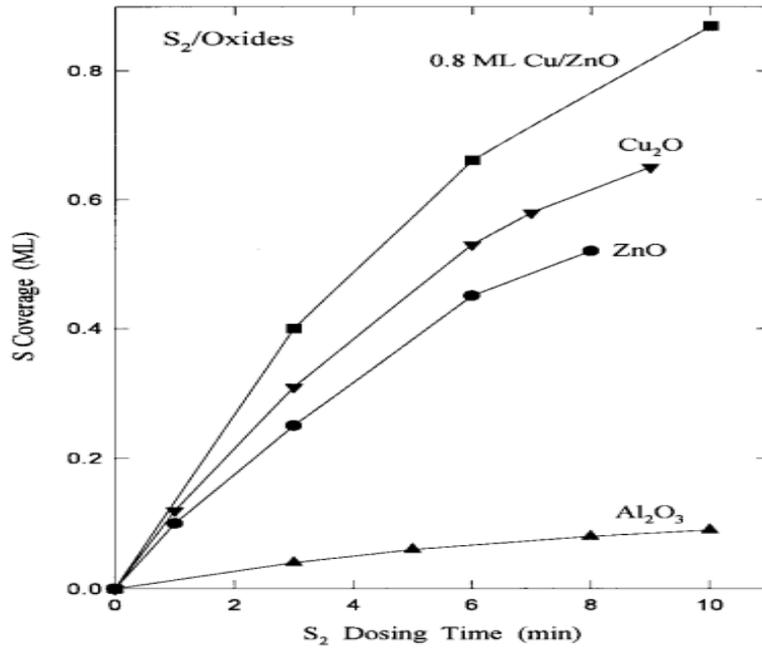


Figure 3: Amount of sulfur adsorbed after dosing S₂ to Al₂O₃, ZnO, Cu₂O and Cu_{0.8}/ZnO at ~300 K (Rodriguez *et al.*, 1998)



This happens as the sulfur stays on the surface of the oxide allowing the process to be repeated for a specific period until the interstices between the oxide’s particles are full. Due to S⁰ build-up and water hydration loss, ferric iron (iron sponge) activity is reduced to about one-third per each regeneration cycle (Kohl *et al.*, 1997). The removal efficiency of this technique depends mostly on the temperature, moisture content and pH of the material used during the purification process. The use of ferric oxide is advantageous as it is cheap and the easiness of operation and maintenance. While the disadvantage is the amount of heat released during the regeneration process.

2.7 Absorption of CO₂ and H₂S by Biochar

Biochar can be defined as a carbon-rich product formed from thermal decomposition of organic material under a limited supply of oxygen (O₂) and at relatively low temperatures < 700°C (Hale *et al.*, 2011). Normally recognized as a multifunctional material, biochar has been explored for agricultural and environmental applications. Biochar is also known to act as a super sorbent for organic contaminants in soil/ sediment. The use of biochar has also been

recommended for various horticultural contexts. It acts as a sponge in the soil, absorbing and retaining water, gases and solutions. Adding biochar to the soil helps in promoting the growth of vegetation by improving soil chemical properties which includes nutrient retention and nutrient availability. It also improves hydrophysical soil characteristics (bulk density, soil permeability, field capacity) and biological properties (Surda *et al.*, 2016). Biochar research has considerably progressed with significant key findings particularly on agronomic benefits, carbon sequestration, greenhouse emissions, soil quality, soil fertility, soil acidity, soil salinity, etc.

Lehmann *et al.* (2015) with further research into biochar- compost mixes and co- composted biochar as soil amendments. Another important fact about biochar is its resistance to attack and decomposition by microorganism, the main reason being its carbon atoms are firmly bound to one another. Other studies to investigate the removal of H₂S and CO₂ from biochar and other carbon-rich substrates have been conducted. Lin *et al.* (2001) experimented on the removal of H₂S from coal bottom ash. The results showed each gram of coal ash could remove up to 10.5 mg of H₂S. In another study Sethupathi *et al.* (2017), tested biochar as a potential adsorbent to CH₄, CO₂ and H₂S gases. This was done by studying the breakthrough times of H₂S, CO₂ and CH₄ for different biochar obtained from oak, perilla and soybean and the simultaneous removal of multiple gases.

The results concluded that CH₄ was not well adsorbed by the subjected biochar whereas CO₂ and H₂S were successfully captured. Table 4 as described by Sethupathi *et al.* (2017) shows the adsorption capacity of biochar during the experiment. Thus, it has the potential to be used as a substrate for the biogas purification process. Juárez *et al.* (2018) investigated the possibility of purifying biogas from a small-scale biogas plant by entrapping CO₂ and H₂S using biomass ash. The results showed that CO₂ was trapped for a few hours while it took H₂S up to 34 days with H₂S absorption in the range of 0.56 - 1.25 kg ton⁻¹ of ash.

Table 4: Adsorption capacity of biochar during simultaneous and single-gas presentation (Sethupathi *et al.*, 2017)

Biochar	Simultaneous			Single		
				H ₂ S	CO ₂	CH ₄
Perilla	0.208	0.126	0.000	0.537	2.312	0.099
Korean oak	0.022	0.027	0.000	0.178	0.597	0.092
Japanese oak	0.018	0.012	0.000	0.167	0.379	0.064
Soybean stover	0.072	0.082	0.000	0.308	0.707	0.094

2.8 Performance Analysis of Other Purification Methods

Chemical, biological and physical methods have been employed for biogas purification. These methods as studied by Iovane *et al.* (2014), Ryckebosch *et al.* (2011) and Syed *et al.* (2006) are as summarized in Table 5, have a considerable improvement in the quality of biogas produced. Factors that were considered were cost, efficiency and environmental effects of byproducts. Biogas purification from acid gasses CO₂ and H₂S using water scrubber reduced more H₂S than CO₂ because H₂S dissolves better than CO₂ in water with the RE of 38.6% H₂S and 21.2% CO₂ (Islamiyah *et al.*, 2015). Water scrubbing had shown significant removal efficiency of H₂S and CO₂. However, this method had performed poorly due to gas leakage from the scrubber.

In another study using soil filtering characteristic, it was observed that the H₂S removal efficiency was almost 100% at all gas flow rates for Allophonic soil, Brown soil and Black sand, followed by Typic sand (around 90 - 100%) (Pham *et al.*, 2019). The study showed that a selection of New Zealand soils with high iron content could potentially be used to construct inexpensive and straightforward H₂S adsorption beds to enhance biogas quality. The H₂S removal efficiency of used soil materials can be improved by exposing them to the atmosphere which adds to the formation of iron oxide which reacts with H₂S. Also, results from Kandola *et al.* (2018) showed that volcanic ash can also be used as a component for the removal of H₂S and NH₃, with the removal efficiency of 80% for H₂S and 100% for NH₃. Moss plant like any plant absorbs CO₂ and releases O₂ to the atmosphere. Due to its large volume to surface ratio, the level of O₂ released is expected to be high in comparison with CO₂ absorbed thus leading to the formation of the oxide. Moss plants as shown grow mostly in a waterlogged environment; therefore, traces of CO₂ and H₂S are expected to be absorbed in this environment. Measuring the net exchange of CO₂ at the surfaces of three dark feather moss and three exposed sphagnum

moss sites in a black spruce forest, photosynthesis by moss accounted for 10 to 50% of whole-forest gross CO₂ uptake measured simultaneously by eddy co-variance (Goulden *et al.*, 1997). Various biological methods for the removal of H₂S by biotrickling filters, biofilters and scrubbers from emission sources of industrial and agricultural have been experimented and studied by Chung *et al.* (1996) and Jensen *et al.* (1995), their main setback has been more extended adaptation period of (> 7days) and lower oxidative rates (Yang *et al.*, 1994).

Table 5: Advantages and disadvantages techniques for biogas purification

Technology	System	Advantages	Disadvantages
Physical	Adsorption on activated carbon	High removal efficiency	Expensive investment and operation
		Low operation temperature	CH ₄ losses
	Membrane separation	High loading capacity	H ₂ O and O ₂ needed to remove H ₂ S
		Removal of >98%, CO ₂ is also removed	Expensive operation and maintenance (fouling problem)
Water scrubbing	Water scrubbing	Light in weight	Complex
		Cheap when water is available (not regenerative)	Difficult technique
Chemical	Caustic soda	CO ₂ is also removed	Clogging of the absorption column possible due to bacterial growth.
		No special chemicals requirement.	High consumption of water (if there is no regeneration)
		Easy in operation.	CH ₄ losses
		Low electricity requirement	Expensive investment & operation
		Smaller volume, less pumping, (compared to absorption in H ₂ O)	More difficult technique
		Low CH ₄ losses	Not regenerative

Technology	System	Advantages	Disadvantages
Biological	Iron salts	Cheap investment Low electricity and heat requirements Simple operation and maintenance No air in biogas	Low efficiency Expensive operation (iron salt) Changes in pH/temp not beneficial for the digestion process Correct dosing is difficult
	Internal desulfurization	Cheap investment Low electricity and heat requirements, No extra chemicals or equipment required Simple operation and maintenance	Concentration H ₂ S still high Excess O ₂ /N ₂ in biogas implies difficult upgrading or additional cleaning Overdosing air results in explosive mixture Difficulties in controlling the operational parameters
	External single stage	Simple, flexible design Low capital Low operation and maintenance costs	clogging dilution with the inert N ₂ gas and excess O ₂ Explosive risk
	External two stage	More than 99% removal efficiency No risk of N ₂ and O ₂ mixing with biogas	Complex High capital and operational costs

2.9 Biofiltration Design and Operating Parameters

Biofiltration refers to the treatment of waste air or water using biological technologies. Biofilter can be defined as a layer of biologically active media, usually of natural origin. The composition of filter particles is mostly soil, compost, peat, wood chips, tree bark and heather (Sercu *et al.*, 2006). According to Delhoménie *et al.* (2005) biofiltration design can be of two types; open designed biofilter and enclosed design biofilter. The difference between the open design and closed is the surface area and direction of the flow of gas. With the open design, it requires a large area with only ascending gas flow and is usually installed outside. While with a closed design, the volume is more restricted and can have either ascending or descending inlet gas flow. Some of the main advantages of using biofilter include low operating costs and have less impact on the environment which is attributed to their self-containment. The disadvantage includes the high pressure drops, less suited when the concentration of contaminants is too high and deterioration of the packing material over time.

It has also been reported that over time clogging may occur due to the difficulties to control moisture, pH and accretion of excess biomass in the packing material (Devinny *et al.*, 2017; Mannucci *et al.*, 2012). The effectiveness of a biofiltration unit depends on various factors; microbial population, type of material used for packing and type of enrichment during the inoculation process. Each factor plays a vital role in elimination capacity, removal efficiency and overall outcome of the removal. Once the biofilter becomes operational, the performance efficiency depends on temperature, moisture content, pH, flow rate, containment loading rate and structure (Kim *et al.*, 2008). The influence of each parameter is described hereafter.

2.9.1 Temperature

A packed bed is mainly governed by the difference in temperature between the inlet gas and the outdoor air. The heat generated by exothermic biological reaction tends must also be taken into account. According to Wani *et al.* (1999), optimum operating temperature for biofiltration applications is around 35 - 37°C but in most cases, biofilters operate at a temperature range of 20 - 45°C (mesophilic range). With the use of microbial organisms, the temperature must be consistent with microbial requirements. For example, *Thiobacillus denitrificas* and *Thiobacillus novellus* tend to thrive mostly in the temperature range 10 - 39°C with an optimum range of around 28 - 35°C (Vlasceanu *et al.*, 1997).

2.9.2 Moisture Content

Moisture content in the packed bed biofilter (bioreactor) is optimum at around 40 – 50% as studied by López *et al.* (2012). It is essential for the survival and metabolism of the resident microorganisms and improves the filters buffer capacity which enables microbial growth. Excessive moisture can lead to pressure drops, bed desiccation and the formation of anaerobic zones, whereas less moisture leads to a significant drop in removal efficiency. According to Delhoménie *et al.* (2005), the factors affecting the bed moisture content includes;

- (i) Inlet relative humidity
- (ii) Water holding capacity of filtering material
- (iii) Gas flow rate through the bed
- (iv) Exothermicity of the reaction which tends to desiccate the bed

2.9.3 pH Condition

During biofiltration of H₂S oxidation by most bacteria and solubility of H₂S in water can cause a pH decrease and hence acidic environment. In some cases where the efficiency of H₂S removal is affected due to a decrease in pH, a buffer solution is added. In general, microorganisms have a specific optimum range of pH for their metabolic activities: pH 5 – 9 for bacteria and pH 2 – 7 for fungi. The range of pH in most compost beds is between 7 and 8, which is typically preferred by most microorganisms (Shareefdeen, 2005).

2.9.4 Nutrient Supply

Carbon, energy and nutrients (nitrogen, potassium, phosphorus and trace elements) are essential for microbial growth. Organic packing materials, such as compost, tend to have these nutrients. However, during operation with time, these nutrients are gradually depleted (Dumont, 2015).

2.9.5 Pressure Drop

The bed pressure drop is an important parameter in biofiltration it has to be taken into account during estimation of operation costs. Leson *et al.* (1995) reported that there was an increase in energy demand from 7 to 25 kW when the pressure drop increased from 4 to 25 cm of water

within 6 months of operation. Factors that can cause a pressure drop in biofilters include; packing materials, gas velocity (flow rate), biomass growth and biofilter dimensions. The effect of pressure drop in the biofilter includes, clogging, creation of anaerobic zones and can in turn affect the overall performance (Devinny *et al.*, 2017). In a long biofilter operation, the increase in pressure drop due to extra biomass and bed compaction decreases the biofilter efficiency, which signifies a major drawback of biofiltration. Naturally, bioactive media such as; soil, compost, or peat contain microorganisms that have been studied to show biodegradability of contaminants. Therefore, they have been effectively employed in bioremediation of contaminated sites.

As the result, it led to the development of soil biofilter, in which soil with low clay and high organic carbon content is packed in a bed and contaminated air passes through the soil bed to biodegrade the air contaminants. Soil biofilter (soil compost reactor) are filtering systems whereby beds of material are arranged such that perforated pipes can deliver the discharge air, as it passes through the moist, aerated biological material. At this stage, the pollutant gases adhere to the soil particles by either dissolving them into soil solution or by exposing them to microbial digestion (Nelson *et al.*, 2011). The soil contains physical and chemical characteristics to support pollutant removal and microbial activities.

CHAPTER THREE

MATERIALS AND METHODS

3.1 Equipment and Accessories

LZB-3WB Gas rotameter, (Mill Gas counter, Ritter Biogas-meter), Geotech Biogas 5000 Gas analyzer, Sleeve, Moss plant sample from the same location, gravels and pebbles, Polyplastic container (25 cm × 16 cm × 9 cm), soil samples, Grinder, plastic containers for soil and moss sample collection and Biochar to help reduce mold and odor in the filter.

3.2 Sample Collection and Preparation

The soil samples and profile statistics were collected from Tanzania Agricultural Research Institute located in Tanga, Tanzania, as part of the soil survey profile for Kwaraguru Sisal Estate. In total, four soil samples were identified as likely candidates for evaluation based on guidelines for soil classification World Reference Base for Soil Resources 2014 Edition (World Reference Base, 2015) in naming and creating of soil map legends. The moss substrate was collected at the campus as it was during the rainy season since they were easily spotted.

Soil survey database and profile information are presented in Table 6. The selected soil sample contained a high number of metallic micronutrients per kilogram (the amount of metallic nutrient a plant can absorb via its roots), percentage of soil organic carbon and carbon to nitrogen ratio. The soil samples with the high composition of extractable micronutrients (Fe, Zn, Cu and Mn) from each profile were selected for this study. Exchange Cu mg/kg refers to 1 mg of exchangeable copper that can be absorbed by the roots in 1 kg of soil as nutrients. Other properties, including the percentage of organic carbon %C, carbon to nitrogen ratio C/N and pH, were also considered for the selection. The selected soils were named T1, T2, T3 and T4.

Table 6: Soil database and profile information

Parameters	Coordinates (Lat-Long)			
	-5.42057°S, 38.52185°E	-5.42519°S, 38.52794°E	-5.48036°S, 38.52422°E	
Appearance	Dark reddish-brown	Very dark greyish brown	Dark reddish-brown	
Sample name	T1	T2	T3	T4
Depth (cm)	0-15/20	20/25-40	0-15/20	15/20-40
Clay %	62	40	50	58
Texture class	Clay	Clay	Clay	Clay
Bulk density g/cm ³	1.02	1.34	1.18	1.21
pH H ₂ O	5.2	6.9	5.4	5.4
Exch. Cu mg/kg	7.47	7.77	2.25	1.5
Exch. Zn mg/kg	0.99	0.48	1.62	0.36
Exch. Mn mg/kg	16.5	47.1	117.0	39.3
Exch. Fe mg/kg	33.99	31.29	51.39	57.69
Organic C %	1.49	1.36	1.77	1.10
C/N	6.77	4.69	8.05	6.47

3.3 Filter Preparation

To construct a prototype of the filter, each substrate i.e. soils T1, T2, T3 or T4, biochar and moss was pretreated after collection, to remove unwanted components like roots, plastics and leaves. The filter was designed to provide a high specific surface area for gas reaction with a low-pressure drop over the packed column. A combination of a high content of active ingredients favors a substantial sulfide binding capacity (Skerman *et al.*, 2017). Each filter contained one of four types of soil (T1, T2, T3 or T4) sieved at less than 400 μm with variable mass (100 g, 150 g or 200 g); 100 g of biochar (charcoal) dust sieved at less 350 μm and 545 g of naturally grown moss plant collected from the damp sidewalk during the rainy season. The packed bed arrangement of the substrates was adopted from Pham *et al.* (2019), the study demonstrated the removal of H₂S using local soil materials from biogas produced by anaerobic digestion of animal wastes. In this study, 700 g layer of small and medium gravels was added above the aerator to prevent blockage by overlying filter material. Moss plant was added as a top layer, with soil and biochar dust as preceding layers below it in order to ensure active gas exchange, growth and sustainability of the filter. The substrates were packed into poly-plastic containers each with the dimensions (25 cm \times 16 cm \times 9 cm) with an airtight cap to cover the top part; the container was transparent to allow just enough light in the filter to aid photosynthesis reaction of moss plants.

An inlet port for the introduction of unpurified gas was inserted at the bottom part connected to the aerator (20 cm long) to ensure homogeneous distribution of the inlet gas across the face of the bed. A step by step preparation of the filter is as shown in Fig. 4.



Figure 4: Preparation of the biofilter

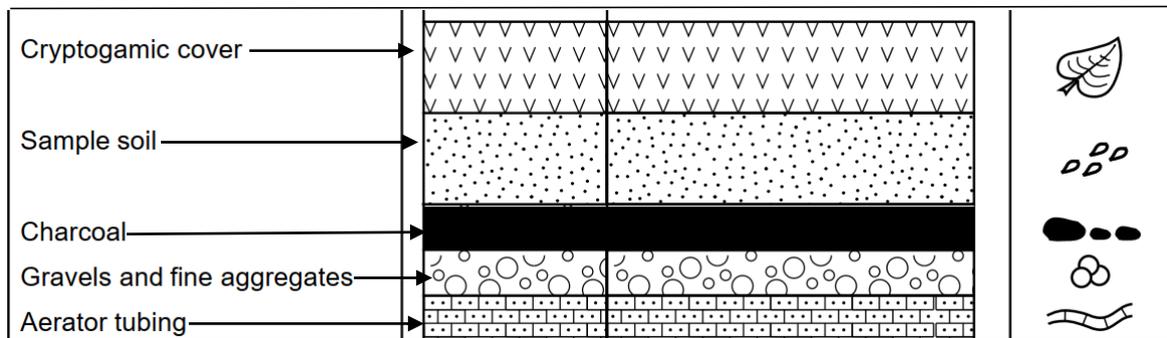


Figure 5: Schematic diagram of substrates arrangement in the filter

The bed included soils with a high amount of micronutrient content and %C, biochar dust (charcoal) which contains unmodified activated carbon and moss substrate. The substrates were arranged in layers based on the role of each substrate in gas sorption efficiency and regenerative capacity. Filter fabrication was conducted at room temperature to ensure all the humid condition present in the moss plant is preserved.

The humid condition in the filter is essential to ensure microbial action and enhance the sorption of CO₂ and H₂S. Xie *et al.* (2017) showed that the presence of soil moisture content results in increased removal capacity for H₂S in a soil biofilter. The presence of water has also

shown a beneficial effect on the overall temperature catalytic performance of activated carbon for the oxidation of H₂S to sulfur (Primavera *et al.*, 1998). After fabrication, the filter was then closed and sealed to begin measurements. It was designed to require no energy during its operation.

3.4 System Operation

Two biogas reactors L1 and L2 available at private premises were used for experimental testing of the biofilter. Table 7 depicts the features of both digesters as well as the average composition of raw biogas which was comparable by methane and carbon dioxide contents but slightly different by ammonia and hydrogen sulfide concentrations. In our on-site tests, biogas flow was allowed to pass through the filter media contained in a rectangular plastic container. The block diagram of the experimental set up is shown in Fig. 6. The on-site set up during the experiment is as shown in Appendix 1.

Table 7: Domestic biodigesters used for the analysis

Digester type	Digester volume (m ³)	Feedstock	Volume gas column (m ³)	Max pressure (mbar)	Raw gas composition
L1	16	Domestic sewage and garden wastes	4	107.8	68–72% CH ₄ , 38 – 40% CO ₂ , 6 – 14 ppm NH ₃ , 498 – 913 ppm H ₂ S
L2	9	Rougher garden wastes and overflow from L1	0.8	84.3	64–66% CH ₄ , 34 – 38% CO ₂ , 3 – 7 ppm NH ₃ , 80 – 110 ppm H ₂ S

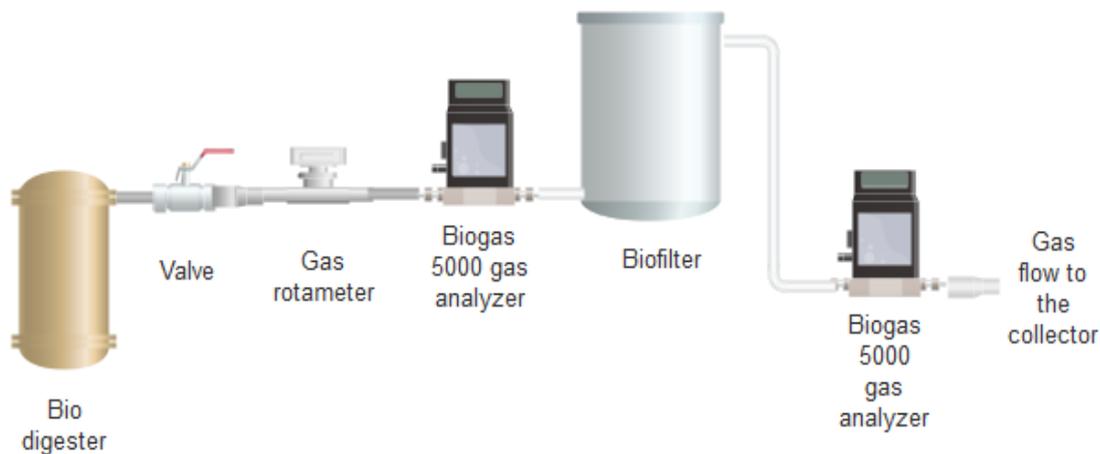


Figure 6: Photo and schematic diagram of the experimental setup

The gas flow rate was controlled using the gas regulator and LZB-3WB rota-meter. The gas composition was recorded before and after the filter using a portable gas analyzer (GA5000 gas, Geotech, England). The overall pH of the filter measured before the experiment was 6.8. Experimental analysis by Nelson *et al.* (2011) revealed that for the regular operation of soil-based biofiltration for air purification, the pH levels should be maintained at around 7 to 8, to prevent the formation of acids from the degradation of inorganic gases.

The tests were divided into three parts. The first part was conducted to analyze the effect of soil type on biogas purification to determine the sorption capacity of the adsorbents. The second part was aimed to analyze raw gas adsorption by each substrate and the third part was to summarize the role of each adsorbent in gas purification which was conducted with flow rates of 80 and 100 ml/min during times 0-150 min for each filter in ambient condition. The arrangement of these substrates in the filter is as shown in Fig. 5.

To examine the performance of each substrate in a filter, raw biogas was allowed to pass through a 5 g sample packed in airtight 5 ml plastic tube at a constant flow of 100 ml/min, the inlet and outlet concentrations H_2S , CO_2 and NH_3 were measured and the readings were recorded in a 10 min interval for 80 min. A small sample mass had to be used to ensure the maximum surface area for adsorption and to avoid a very high-pressure drop which is not recommended for biofilter operation. For example, Abatzoglou *et al.* (2009) reviewed from various studies that commercially packed biofilters are engineered to provide high specific surface area, having a low-pressure drop and together with a high content of active ingredient, provide high sulfide binding capacity.

3.5 Filter Performance Parameters

The performance of the developed biofilter was determined in terms of removal efficiency (RE) and sorption capacity (SC). The CO₂, NH₃ and H₂S concentrations of treated gas at the outlet were analyzed at 10 min intervals for each test, RE and SC were calculated using Eq. (3.1) and Eq. (3.2) respectively. Whereby C_i and C_f are the initial and final concentration of H₂S (CO₂ or NH₃) as measured before and after filtration respectively; Q is the flow rate (m³·h⁻¹), M is the atomic mass of sulfur, V_{mol} is the molar volume of the gas (L·mol⁻¹) under standard conditions. A breakthrough time (BT) in hours was recorded as the time when C_f approached 50% of C_i, where no significant adsorption of sulfur by the substrate was observed.

$$\text{RE (\%)} = \frac{C_i - C_f}{C_i} \times 100 \dots\dots\dots (1.1)$$

$$\text{SC} \left(\frac{\text{g sulfur}}{100\text{g sorbent}} \right) = Q \times \frac{M}{V_{\text{mol}}} (C_i - C_f) \text{ BT} \dots\dots\dots (3.2)$$

To elucidate the role of each substrate, special tests were conducted as described in Section 3.4; the SC of each biofilter component was calculated by using Eqn. 3.2. Where C_i and C_f are the initial and final concentration of H₂S, CO₂ or NH₃ as measured before and after filtration respectively; Q is the flow rate (m³ h⁻¹), M is the atomic mass of sulfur, V mol is the molar volume of the gas (L mol⁻¹) under ambient conditions. A breakthrough time (BT) in hours was recorded as the time when C_f approached 50% of C_i, where no significant adsorption of sulfur by the substrate was observed.

CHAPTER FOUR

RESULTS AND DISCUSSION

4.1 Soil Type Effect on Biogas Purification

Different types of soil, T1, T2, T3 and T4, of the same soil mass 100 g were tested in biogas purification at a constant flow rate of 80 ml/min. The masses of other substrates, 100 g of biochar and 545 g of moss, were kept constant during fabrication of the filter. The biogas composition before and after the filter was monitored every 10 min for 150 min.

The results as depicted in Fig. 7 illustrates the removal efficiency for CO₂, H₂S and NH₃ from each soil type at a constant flow rate with the initial concentrations, as shown in Table 7. This was conducted to determine the filter that showed a high percentage on average for the removal of all these impurities. The results indicate that filters with T3 and T4 soils had the most substantial average removal of CO₂ at 76% and 75% respectively. T3 filter also showed a significant RE of NH₃ at 72% on average over the entire period than other soil types. For H₂S removal filters T4 and T3 showed the largest RE at 97% and 93% respectively. The reason for higher RE exhibited by soils T4 and T3 is the highest total content of extractable iron compared to T1 and T2, as shown in Table 6. As it has been demonstrated in Eqn. 2.3 high iron content in the soil contributes to more significant interaction with H₂S impurities. Presence of other extractable micronutrients (Zn, Cu and Mn) also favors in reacting with H₂S.

The test results accord well with an investigation Rodriguez *et al.* (1998) where it was shown that H₂S and S₂ reacted faster with CuO, ZnO than corresponding sites of alumina (Al₂O₃) based on the bandgap size and chemical reactivity. Also, it was further observed by the test results accord well with an investigation Rodriguez *et al.* (1998) where it was shown that H₂S and S₂ reacted faster with CuO, ZnO than corresponding sites of alumina (Al₂O₃) based on the bandgap size and chemical reactivity. Iron-rich and zinc-containing soils effectively removed H₂S from coal-derived natural gas (Ko, 2008; 2011). The soil T3 showed higher interaction with H₂S.

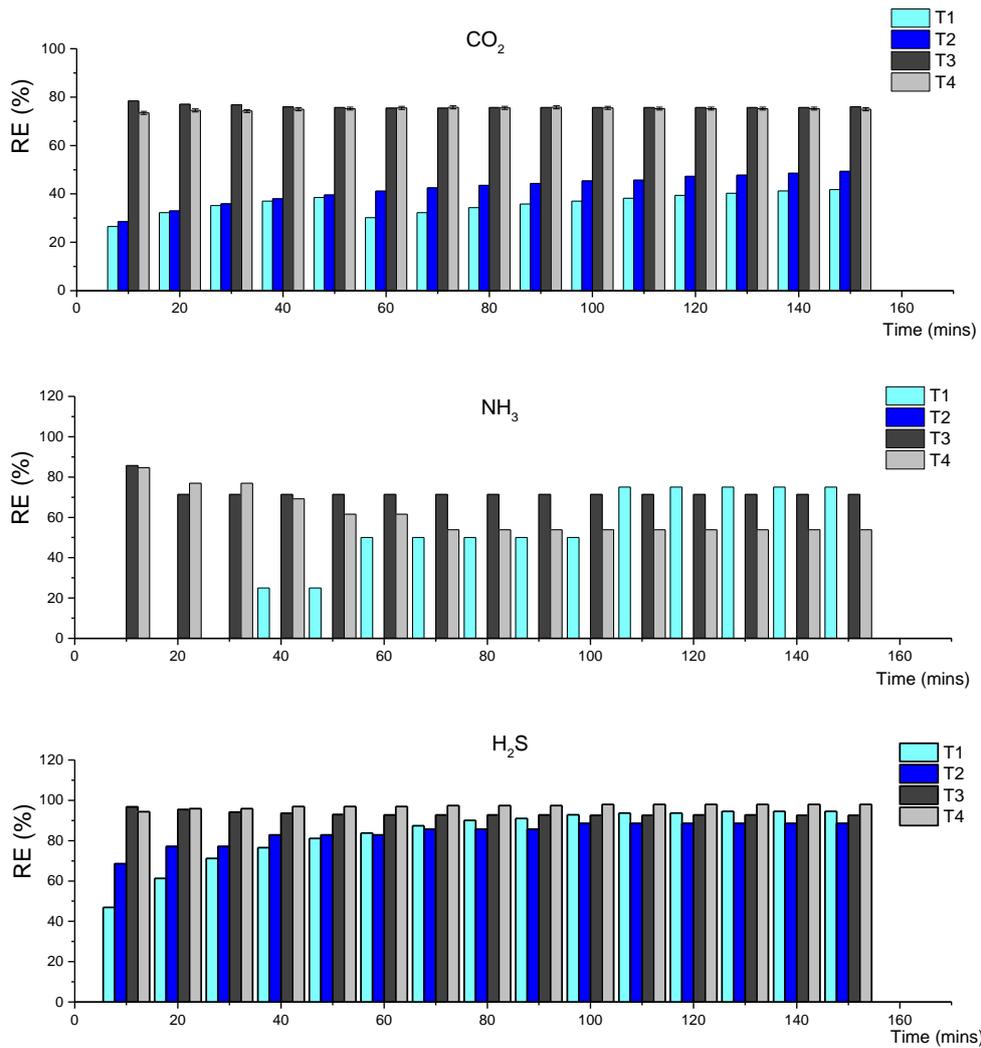


Figure 7: Biogas purification by filters with different soil samples: RE versus operating time. Test conditions: $Q = 80$ ml/min, $m = 100$ g, $T = 19^{\circ}\text{C}$, $C_0 = 36.4\%$ for CO_2 , 13 ppm for NH_3 , 836 ppm for H_2S

Table 8: Soil types performance in biogas purification, RE, average over operating time ($Q = 80$ ml/min)

Gas analyzed	Initial concentration (Ci)	RE, %, average over time 2.5 hrs			
		T1	T2	T3	T4
CO ₂	36.4 – 40.0%	36.0	42.0	76.1	75.1
NH ₃	7 - 13 ppm	56.3	nd	71.4	56.4
H ₂ S	498 - 836 ppm	83.5	84.0	93.3	97.1

*nd – not determined.

The dark reddish-brown coloration of the soil indicates richness in the crystalline structure of iron oxide minerals which have a strong influence on H₂S removal capacity (Skerman *et al.*, 2017). Also, Lasocki *et al.* (2015), observed that the iron oxide present in soils and activated

carbon (charcoal) as beds in filters reduced almost 100% of H₂S in a 30 min exposure period in the Laboratory-scale investigation. Other factors that contributed to better performance of T3 soil were high levels of soil organic matter, organic carbon percentage and C/N ratio of the soil compared to other soils. The presence of organic matter improves soil aggregate and structural stability which are significant for infiltration of water and aeration into the soil, thus enabling the high surface area of reaction (Lefèvre *et al.*, 2017). Soil organic carbon is vital in improving soil structure and provides habitat for soil biota, which together ensures sustainable yields as they retain water and nutrients (Lal, 2009; Lorenz *et al.*, 2007). The level of C/N in the soil determines the rate of decomposition of organic matter and soil productivity, which was studied by using paddy fields by Li *et al.* (2016). Therefore, T3 soil was subjected to further tests in the effect of soil mass and flow rate to the removal efficiency.

4.2 Effect of Varying Soil Mass on Removal Efficiency

Further tests were performed to identify how the mass of the soil affects the removal of CO₂, NH₃ and H₂S from raw biogas. The experiment was conducted only T3 soil, which exhibited better results than other types of soils. The masses of other substrates and flow rate were kept constant at 100 ml/min. The filters that differed in soil masses were used, whereby; T3–100, T3–150 and T3–200 referred to T3 soil substrate with a mass of 100, 150 and 200 g respectively. The initial concentration of raw gas was in the range of 36.4 – 37.5 % for CO₂, 7 - 13 ppm for NH₃ and 498 - 836 ppm H₂S. Soils had the same particle size of <400 µm.

During operation time of 150 min, the outlet impurities were recorded as the raw gas passed into the filter. Figure 8 shows the removal efficiency of CO₂, NH₃ and H₂S gases. For CO₂, the removal efficiency was approximately 99.7% for T3 – 200 over the operation time. When the mass of the soil was further lowered to 150 g, the removal efficiency dropped to about 75% and further to nearly 70% for the filter with 100 g soil.

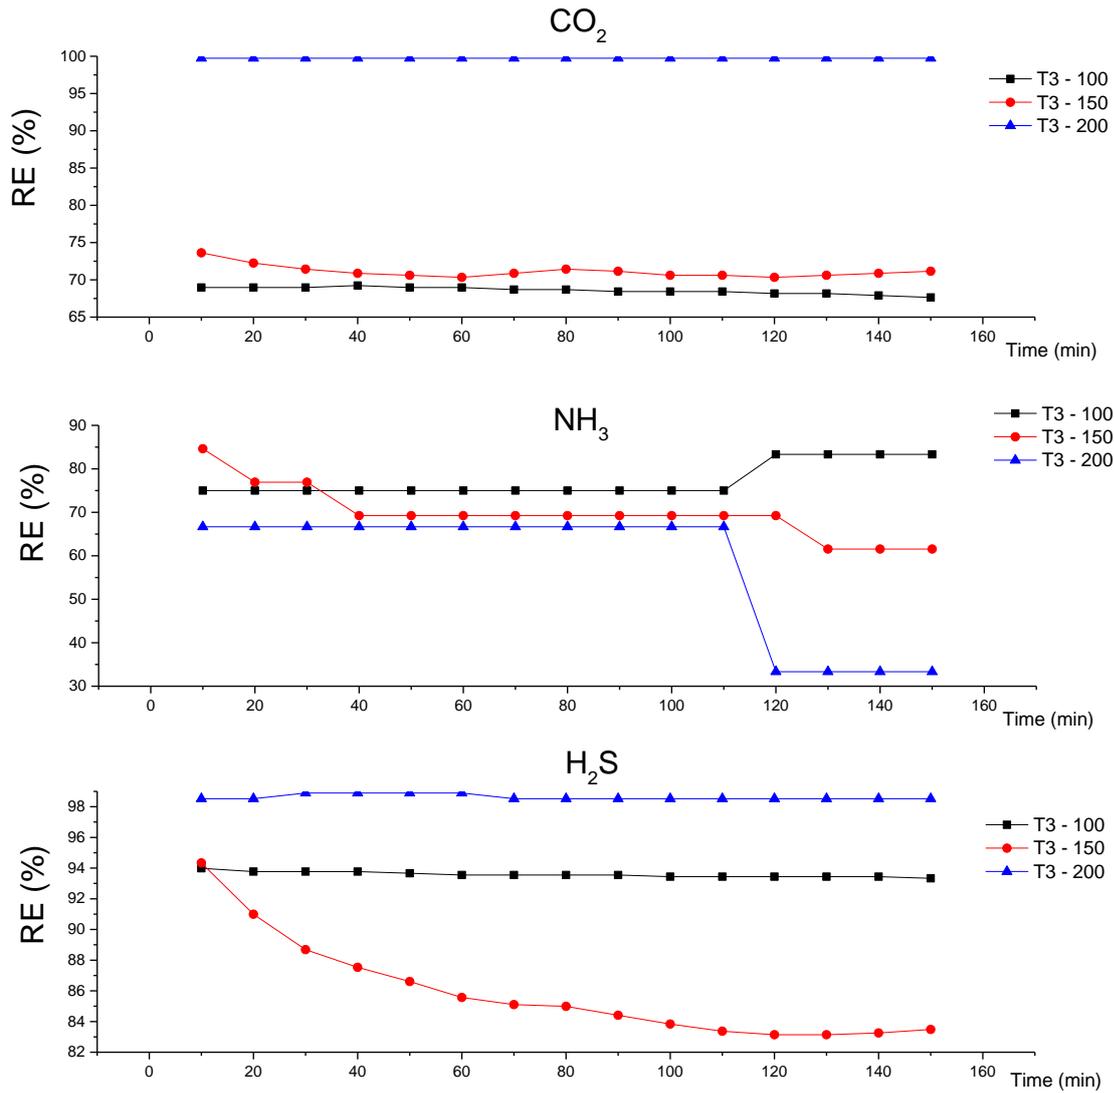


Figure 8: Soil mass effect of the filter T3. Test conditions: $Q = 100$ ml/min, $m_1 = 100$ g, $m_2 = 150$ g, $m_3 = 200$ g $P = 10$ kPa $C_0 = 37.5\%$ for CO_2 , 13 ppm for NH_3 , 836 ppm for H_2S

For the case of NH_3 ; RE was 83% but dropped to 33% for T3–200 and as high as 83% to 77% drop for T3–150. The filter T3–100 had a maximum RE of 80% before saturation. After 120 min, no more NH_3 adsorption was observed. It is supposed this sharp decrease could be due to the drop in the initial concentration of the gas to the lowest amount recorded of 7 ppm and that low ammonia concentration measurement occurred at the sensitivity limit of the gas analyzer. Filter T3–100 has a large surface area of reaction, unlike other filters with substantial mass, which are highly compacted thus having less adsorption rate.

As it was demonstrated by Kent *et al.* (2000), filter beds with small particles size offer a high specific surface area for reaction and thus favoring nitrification and microbial activity, but also they tend to constitute a greater resistance to gas flow which increases as biomass grows in bed porosities (Yang *et al.*, 1994). On the other hand, large particles have low-pressure drop since the gas flow is not blocked, but offer fewer surface sites for oxidation reaction, therefore it can lead to lower elimination performances (Delhom nie *et al.*, 2002). Also, NH₃ has a low Henry's constant ($H_{20^{\circ}C} = 5.6 \times 10^{-4}$) (Perry *et al.*, 2008) and a protonation constant pK_a , 20°C of 9.23 (Weast *et al.*, 1984). These values make NH₃ in biofilters to be partly retained onto the surface of carrier material by adsorption and by absorption of water fraction of the material (Sercu *et al.*, 2006).

The T3–100 filter showed higher RE in H₂S than T3-150 and T3–200, which can be explained by the availability of high surface area of adsorption between the gas molecules and the soil adsorbent containing a high content of iron and other cations eg Cu and Zn. Filter T3-200 due to a large mass of soil content has the higher gas retention time of all the filters, as it takes longer for the gas reaction to complete. The large mass of soil may also lead to clogging. It can be effective if the soil is evenly dispersed to allow more gas retention time. The higher retention time was effective in H₂S elimination capacity as it was studied by Yang *et al.* (1994).

From the results, one can conclude, that with T3–100, there was a steady flow of raw gas from the aerator to the subsequent layers, thus having quick reaction time and a greater RE for H₂S and NH₃. On the other side, a large mass of soil causes the filter to be non-porous since the particles are tightly compacted together, resulting in the reduced surface area of reaction and large pressure drop.

4.3 Effect of Biogas Flow Rate on the Biofilter T3 Removal Efficiency

The H₂S, CO₂ and NH₃ removal were further analyzed for filter T3 by considering variation in flow rates of 80 ml/min and 100 ml/min. The filter performance with the soil mass 100 g (T3-100) is shown in Fig. 9. As is seen, quite steady RE behavior is upheld for all three impurities; except a small and casual variation for NH₃ that can be attributed to a small but changeable amount (7–13 ppm) in the raw gas. The CO₂ removal is affected by the flow rate; the RE lowered by 7% from 80 to 100 ml/min. In the case of H₂S, the change of flow rate practically does not influence the RE that remains constant $\approx 94\%$ during the filter operating time. A

summary of removal efficiency at both flow rates is given in Table 8. Also, the effect of the soil mass is taken into account.

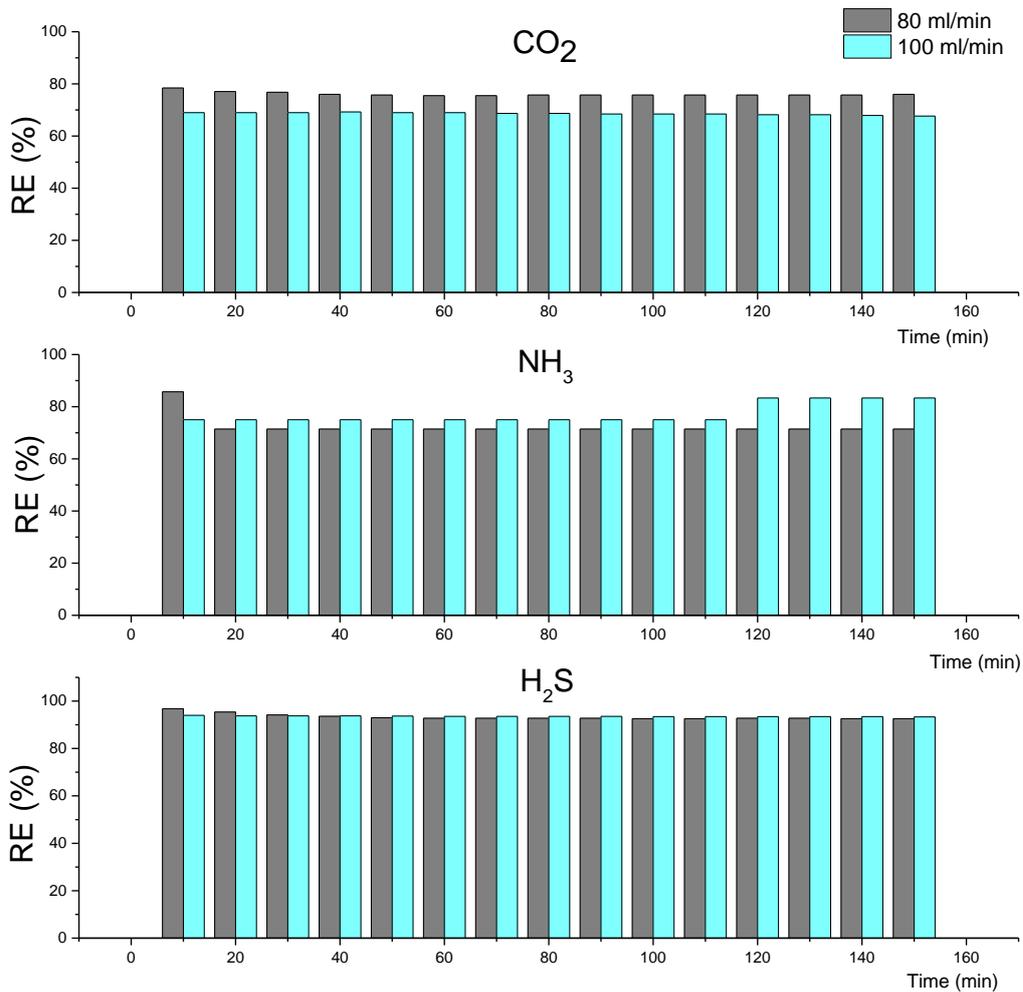


Figure 9: RE of the filter T3–100 at two different flow rates (80 and 100 ml/min). Test conditions: $Q_1 = 80$ ml/min, $Q_2 = 100$ ml/min $m = 100$ g, $P = 10$ kPa, $C_0 = 37.7\%$ for CO₂, 12 ppm for NH₃, 915 ppm for H₂S

The RE for CO₂ was high for the filter with the largest soil mass at both flow rates. This can be attributed to the effect of pressure drop. The pressure drop is high for the most substantial packed bed in comparison to other filters. This, as a result, makes CO₂ concentration as it passes through the packed material in a given time to be significantly low, thus allowing time for maximum adsorption of the gas by the moss substrate. The same can be explained for the RE of CO₂ to be higher for the same flow with T3-150 than T3-100. Meanwhile, with a low flow rate for T3-100 and T3-150 filters, high RE is observed. This can also be as a result of having sufficient reaction time for the adsorption of CO₂ by the substrate.

Table 9: Effect of soil mass and biogas flow rate on the biofilter T3 performance; H₂S removal efficiencies are given as average values over 2 hours operating time

Gas analyzed	Initial concentration (Ci)	Flow rate, (Q, ml min ⁻¹)	RE (average over time), %		
			T3-100	T3-150	T3-200
CO ₂	36.4 – 40.0 %	80	76.1	75.9	99.7
		100	68.6	71.1	99.7
NH ₃	7 - 13 ppm	80	72.4	73.3	50.0
		100	77.2	69.7	57.8
H ₂ S	498 - 836 ppm	80	93.3	97.7	96.7
		100	93.6	85.9	98.6

On average, the RE for NH₃ is high with T3-100 at 100 ml/min and drops as the mass of the filter increases (T3-150>T3-200). Moreover, with the flow of 80 ml/min, there is a slight difference in RE for T3-100 and T3-150, but it drops for T3-200. Joshi *et al.* (2000) demonstrated on a field-scale peat biofilter that NH₃ removal along with sulfur compounds can also be attributed to the adsorption by the acidic nature produced during oxidation of sulfur compounds.

An increase in the flow rate, results in the increase of gas reaction time for the filter with larger mass (T3-150 and T3-200) and lower risk of clogging. But for the filter with a small mass, the effect is reversed as more gas will pass through without been adsorbed by the soil adsorbent. For the T3-100, the RE was considerably high for a low flow rate than a high flow rate. This allows a large number of particles present to interact with H₂S gas, offering more time for oxidation to occur. With a low flow rate, maximum gas reaction time was observed. These results are in agreement with studies from Chung *et al.* (1996) and Singh *et al.* (2011), whereby, data on H₂S removal by combined chemical and microbial solution, showed that RE for H₂S increased with increasing gas reaction time. In the investigation on operational parameters of biofiltration design by Yang *et al.* (1994), it was observed that an increase in loading rate results in to decrease in gas retention time, due to insufficient reaction time between H₂S molecules and the biomass in the filter.

Thus, H₂S RE can be improved by either reducing the flow rate or increasing the soil volume. As seen in Table 9, the best performing filter for all gases by considering average RE was T3-100. Other filters showed better RE for one type of pollutant but less for the other type

measured at either of flow rates. For example, T3-200 showed high RE for CO₂ and H₂S but less with NH₃.

4.4 Analysis of the Function of each Substrate

4.4.1 Sulfur Adsorption Performance of Various Adsorbents

The breakthrough time is used to specify the saturation time of the substrate before it needs regeneration or replacement. Longer breakthrough time implies a better adsorption capacity of the particular substrate (adsorbent) (Chowdhury *et al.*, 2012). It also implies a shorter reaction time. Variations of the adsorbate concentration against the operating time of a filter are known as breakthrough curves (Sethupathi *et al.*, 2017). These curves are presented in Fig. 10a for different biofilter substrates, the soils T3, biochar and moss. The sample was considered saturated when the outlet concentration reached 50% of the inlet.

The H₂S breakthrough time for adsorbents T3 and T4 was both about 80 min, after which it was observed, a minimal variation in sulfur adsorption. Also, for the case of biochar and moss, the H₂S breakthrough time (BT) was 50 min and 20 min respectively. For other adsorbents, T1 and T2, a small change in their concentrations were observed, thus no significant adsorption was detected. The adsorption breakthrough time of T3 and T4 was higher than other adsorbents (substrates). A comparison between initial and final H₂S concentrations is shown for the substrates in Fig. 10b. The sulfur sorption capacity of each substrate was calculated using Eqn. 3.2 and indicated as the amount of sulfur adsorbed per 100 g of the sorbent in Fig10c. As seen, the soils T3 and T4 retain the highest H₂S amount, 20.8, 20.1 g-S/100 g respectively, compared to other adsorbents whereas T1 and T2 soils are practically unable to adsorb sulfur. Regarding biochar and moss substrates, H₂S was partly retained with a sorption capacity of up to 6.0 and 1.8 g-S/100 g respectively. The results are comparable with data by Sahu *et al.* (2011) whereby, the sorption capacity of red mud (RM) sample used for H₂S removal was 2.1 g-H₂S/100 g of RM. High sorption capacity by T3 and T4 is comprehensible, as they both have a high total content of extractable cation, specifically iron and high C/N compared to other soil substrates as shown in Table 6. Summarizing contributions from the three substrates; (soil T3, biochar and moss), the designed SC biofilters T3-100 and T4-100 can be estimated to remove a total of 10.8 and 10.7 g-S respectively.

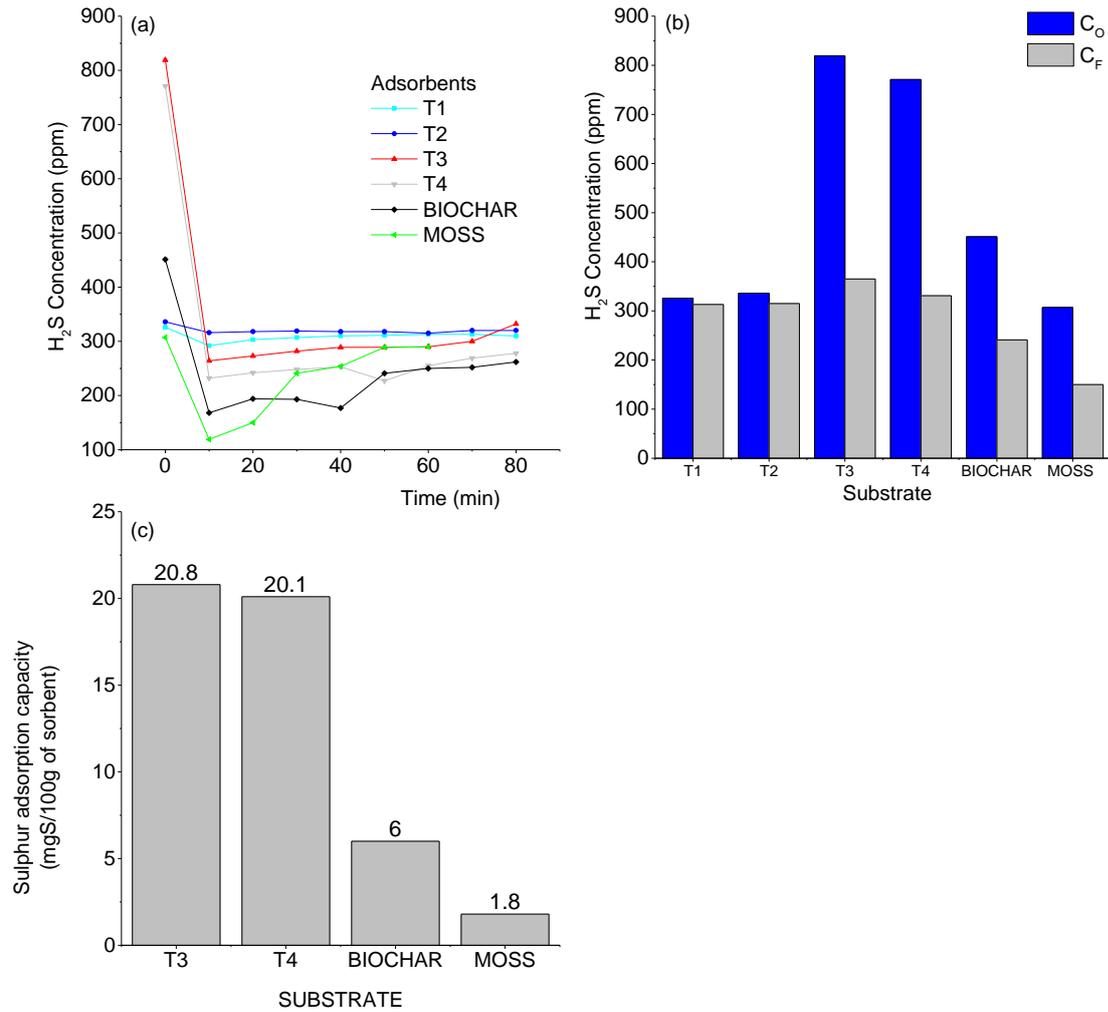


Figure 10: Sulfur removal by various adsorbents: (a) Breakthrough curves, (b) H₂S absorption over breakthrough time and (c) Sorption capacities. Test conditions: $Q = 100$ ml/min, $m = 5$ g, $C_0 = 307$ - 819 ppm for H₂S, Time = 80 min

4.4.2 Moss Substrate Performance in CO₂ and NH₃ Removal

The capacity of a moss substrate on removing CO₂ and NH₃ from biogas was tested under the same conditions as described in the previous sub-section about H₂S sorption. A 59% drop in CO₂ concentration and 38% for NH₃ was recorded during the 60 min of the experiment Fig. 11. For the case of CO₂, moss plants like most cryptogams account for the largest net carbon uptake (photosynthesis minus respiration) from the atmosphere (Chapin *et al.*, 2006; Field *et al.*, 1998). The present study demonstrated moss to be very effective in CO₂ adsorption from raw biogas for 60 min. A low adsorption rate for NH₃ is mainly because moss is non-vascular plant as most ammonia needs to be converted first to ammonium and nitrate by nitrifying

bacteria and absorption by the plant from the soil is done by roots (Joshi *et al.*, 2000). The summary of the results is as shown in Table 11.

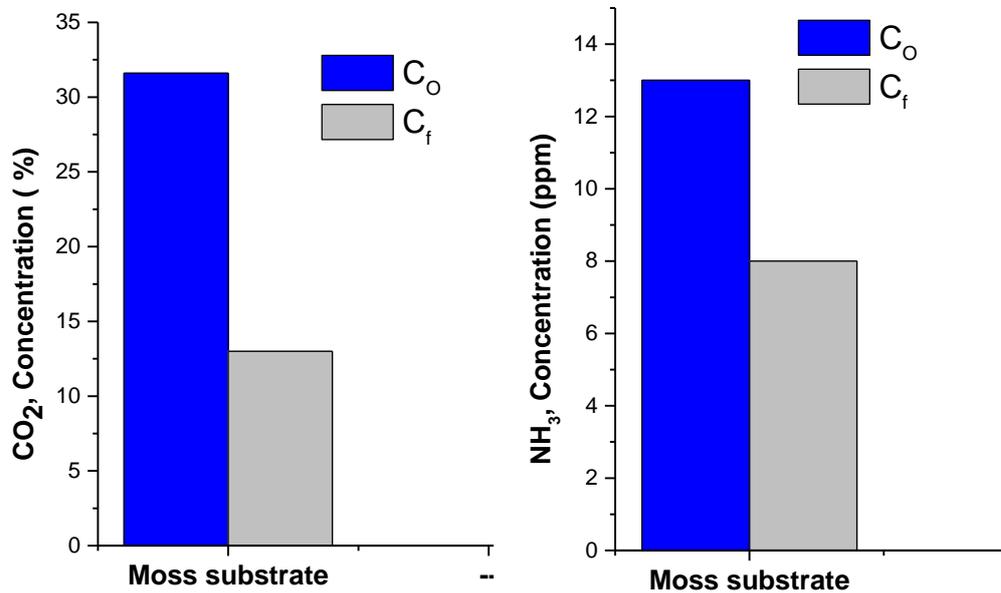


Figure 11: Adsorption of CO₂ and NH₃ by moss substrate in 60 min operation time

Table 10: Summary of BT, SC (g-S/100g of sorbent) for all substrates

Substrate, impurity	BT, min	SC, g-S/100 g sorbent
T1, H ₂ S	<10	n/a
T2, H ₂ S	<10	n/a
T3, H ₂ S	70	20.8
T4, H ₂ S	70	20.1
Biochar, H ₂ S	50	6.0
Moss, H ₂ S	20	1.8
Moss, CO ₂	45	n/a
Moss, NH ₃	40	n/a

4.5 Comparison of Biogas Purification with other Biofilters of Different Media

Biological techniques can be the best alternative in the reduction of impurities in the biogas, because the use of chemicals is limited and it is considered economical and environmentally friendly. Investigations of different media for biogas purification in comparison to our study are summarized in Table 12. In this study, NH₃ was removed to up to 77.2% at a constant flow of 0.006 m³ h⁻¹ (100 ml/min). For CO₂ and H₂S removal, the physical and chemical properties of biochar in the filter have significantly improved the adsorption capacity.

Table 11: Absorption properties of the cryptogamic filter compared to other biofilters

Bed type/Adsorbent	Gas	Impurity Gas	Loading rate	RE (%)	Elimination capacity	Disadvantage	Reference
Peat biofilter	NH ₃	20 ppmv	1.8 g m ⁻³ hr ⁻¹	80	41 g m ⁻³ d ⁻¹	Overloads at a loading rate of 7.9 gm ⁻³ hr ⁻¹ . Prone to channeling and maldistribution Limited ability to neutralize acidic degradation products.	Hartikainen <i>et al.</i> (1996)
Perlite biofilter	NH ₃	20 - 50 ppmv	8.6 g m ⁻³ d ⁻¹ and 21.5 g m ⁻³ d ⁻¹	99.5	NA	Production of NO and NO ₂ at the outlet	Joshi <i>et al.</i> (2000)
Compost and activated carbon as added material	NH ₃	20 – 500 ppmv	0.2 - 40 g NH ₃ /kg d ⁻¹	95.9	NA	For better removal effluent NH ₃ should be <200 ppm.	Liang <i>et al.</i> (2000)
Cow manure compost	H ₂ S	~ 1500ppm	58 m ³ h ⁻¹	80	16 – 118 g m ⁻³ h ⁻¹	High operating costs, clogging to deposition of elemental sulfur	Zicari (2003)
Chemical scrubber converted to biotrickler	H ₂ S	30 - 50 ppm	NA	97	38–127 g m ⁻³ h ⁻¹	High operating costs and further research to reconcile lab-scale and field results.	Gabriel <i>et al.</i> (2002)

Bed type/Adsorbent	Gas	Impurity Gas	Loading rate	RE (%)	Elimination capacity	Disadvantage	Reference
Metal-ferrite sorbents made from heavy metal wastewater sludge	H ₂ S	1% H ₂ S in a mixture of gas.	4000 mL h ⁻¹ g ⁻¹		26.1 g-S/100g by ZF ₆ sorbent	High sulfidation temperature and longer breakthrough time	Tseng <i>et al.</i> (2008)
Biomass ash	CO ₂ and H ₂ S	100 – 600 ppm H ₂ S, 33 – 35% CO ₂	0.56 - 1.25 kg H ₂ S t ⁻¹ Ash 35 kg CO ₂ t ⁻¹ Ash and 135 kg CO ₂ t ⁻¹ Ash.	50 for H ₂ S, not feasible for CO ₂	NA	Not feasible for CO ₂ removal, ashes could not be reused for as fertilizer.	Juárez <i>et al.</i> (2018)
T3, T4 soil substrates	H ₂ S	771 - 819 ppm	0.0048 m ³ h ⁻¹	93, 97	20.8, 20.1 g-S/100g	A constant flow rate <0.006 m ³ /hr to prevent large pressure drop	This study
Moss substrate	CO ₂ , NH ₃ , H ₂ S	CO ₂ - 31.6%, H ₂ S – 307 ppm, NH ₃ – 13 ppm	0.006 m ³ h ⁻¹	59 - CO ₂ , 38 -NH ₃ 68-H ₂ S	1.8 g-S/100 g of sorbent	The flow rate <0.0048 m ³ /hr to prevent intoxication of microbes by NH ₃ and H ₂ S present	This study
Cryptogamic filter	CO ₂ , NH ₃ , H ₂ S	CO ₂ – 38%, NH ₃ – 8.7 ppm, H ₂ S - 819 ppm	0.006 m ³ h ⁻¹	99.7- CO ₂ , 77.2- NH ₃ , 98.6- H ₂ S	11 g-S/100 g	It does not work on high pressure, high flow rate operation and requires water scrubber for removal of excess Oxygen.	This study

Sethupathi *et al.* (2017) observed that the adsorption performance of a fixed bed column was significantly improved by the physical and chemical properties of biochar on CO₂ and H₂S removal. It also revealed that biochar has a relatively low effect on CH₄ adsorption. Therefore, CH₄ content is unaffected during the whole adsorption process. Juárez *et al.* (2018) in his study on biogas purification with biomass ash, found that the ash was successful in removing both CO₂ and H₂S, but to an extent, CO₂ removal was affected by high filter rates. This study has addressed the flow rate to ensure maximum gas reaction time to allow considerable adsorption of CO₂ by biochar and moss substrates. The presence of moisture by which cryptogams thrive provides a humid condition for further removal of CO₂ and H₂S gases. The filter has integrated the physical and chemical properties of these substrates to facilitate the removal of these impurities from the gas.

Other multiple gas removal filters were designed for the removal of more than one pollutant from the gas; results have shown significant removal for one gas but relatively poor for the other gases (Juárez *et al.*, 2018). The primary advantages of biological filters were low energy requirements, mild operations and regeneration capability of the materials (Kim *et al.*, 2004; Vannini *et al.*, 2008). The disadvantage of using these methods was the low flow rate required for operation, additional nutrients were required, clogging of the bed due to sulfur deposit and a small amount of O₂, N₂ and moisture was left in the treated biogas (Zhao *et al.*, 2010).

CHAPTER FIVE

CONCLUSION AND RECOMMENDATIONS

5.1 Conclusion

Biofiltration system integrated with four types of soils, T1, T2, T3, or T4, with biochar and cryptogamic cover, was designed and tested on-site for removal biogas impurities in the form of CO₂, H₂S and NH₃. The function of each substrate was elaborated via a special experimental arrangement. Among the samples, the T3 and T4 soils demonstrated the best H₂S removal with sorption capacities of 20.8 and 20.1 g-S/100 g and RE of 93% and 97% respectively. This good performance of the soils attributed to their high iron content, large cation exchange concentration and organic carbon percentage. Moss and carbon-based material (biochar) showed inadequate H₂S removal, indicating that pure physical adsorption was not efficient on digesters operating at low pressures such as in typical farm. Moss substrate had significantly high CO₂ RE of 59% and as low as 38% for NH₃ during the 60 min of the experiment.

Integrating these substrates in a bed arrangement of a packed biofilter improved the overall adsorption of CO₂, NH₃ and H₂S. The most important advantage of a cryptogamic biofilter over other physical-chemical technologies is that, it is applicable in a wide range of pollutants (impurities), effective in low concentration, can be used under ambient conditions (pressure, temperature and pH), consumes very little energy, materials are easy to obtain, simple to operate and economic. Another advantage is flexibility, as they are quick to respond to the changing pollutant characteristics because of the wide range of microbial metabolic pathways.

5.2 Recommendations

The Combustion of biogas fuel that contains H₂S gas produces intoxicating fumes that are harmful to human health with respiratory ailments such as bronchitis and asthma. As discussed, the solution to this is, therefore, to remove these contaminants from the gas. This study recommends that the biofilter for the removal of biogas contaminants be built adjacent to the biodigesters to provide efficiency, the well-being of the consumers as well as the safety of the environment. The lab experiment on the biofilter performance is also of importance, but in this work, it was not done so far; only on-site tests were conducted. It is recommended to conduct the lab tests at steady conditions for further analysis of biogas impurities adsorption by biofilter components.

Further research on biofilters may help explain the influence of prolonged time and reliability of the filter towards improving it. Also, to enhance the performance of the filter the following tests can be suggested:

- (i) Further tests to be performed on the site at controlled conditions over a long period to verify sustainability of the filter and contaminant removal rate.
- (ii) The effect of moisture and humidity on the filter performance particularly on the settling of the bed materials, gas removal and how it affects the gas calorific value.

REFERENCES

- Abatzoglou, N., & Boivin, S. (2009). A review of biogas purification processes. *Biofuels, Bioproducts and Biorefining*, 3(1), 42-71. doi: 10.1002/bbb.117 Retrieved from <https://onlinelibrary.wiley.com/doi/abs/10.1002/bbb.117>
- Adamo, P., Giordano, S., Vingiani, S., Castaldo Cobianchi, R., & Violante, P. (2003). Trace element accumulation by moss and lichen exposed in bags in the city of Naples (Italy). *Environmental Pollution*, 122(1), 91-103. doi: [https://doi.org/10.1016/S0269-7491\(02\)00277-4](https://doi.org/10.1016/S0269-7491(02)00277-4) Retrieved from <http://www.sciencedirect.com/science/article/pii/S0269749102002774>
- Agegnehu, G., Bass, A. M., Nelson, P. N., & Bird, M. I. (2016). Benefits of biochar, compost and biochar–compost for soil quality, maize yield and greenhouse gas emissions in a tropical agricultural soil. *Science of The Total Environment*, 543, 295-306. doi: 10.1016/j.scitotenv.2015.11.054 Retrieved from <https://doi.org/10.1016/j.scitotenv.2015.11.054>
- Ahmad, M., Rajapaksha, A. U., Lim, J. E., Zhang, M., Bolan, N., Mohan, D., . . . Ok, Y. S. (2014). Biochar as a sorbent for contaminant management in soil and water: A review. *Chemosphere*, 99, 19-33. doi: 10.1016/j.chemosphere.2013.10.071 Retrieved from <https://doi.org/10.1016/j.chemosphere.2013.10.071>
- Bargagli, R. (1989). Determination of metal deposition patterns by epiphytic lichens. *Toxicological & Environmental Chemistry*, 18(4), 249-256.
- Bargagli, R., Monaci, F., Borghini, F., Bravi, F., & Agnorelli, C. (2002). Mosses and lichens as biomonitors of trace metals. A comparison study on *Hypnum cupressiforme* and *Parmelia caperata* in a former mining district in Italy. *Environmental Pollution*, 116(2), 279-287.
- Bauer, F., Persson, T., Hulteberg, C., & Tamm, D. (2013). Biogas upgrading – technology overview, comparison and perspectives for the future. *Biofuels, Bioproducts and Biorefining*, 7(5), 499-511. doi: 10.1002/bbb.1423 Retrieved from <https://doi.org/10.1002/bbb.1423>

- Brock, T. D., & Gustafson, J. (1976). Ferric iron reduction by sulfur-and iron-oxidizing bacteria. *Applied and Environmental Microbiology*, 32(4), 567-571.
- Broekhuis, R. R., Koch, D. J., & Lynn, S. (1992). A medium-temperature process for removal of hydrogen sulfide from sour gas streams with aqueous metal sulfate solutions. *Industrial & Engineering Chemistry Research*, 31(12), 2635-2642. doi: 10.1021/ie00012a002 Retrieved from <https://doi.org/10.1021/ie00012a002>
- Cape, J. N., van der Eerden, L., Fangmeier, A., Ayres, J., Bareham, S., Bobbink, R., . . . Wolseley, P. (2009). Critical Levels for Ammonia. *Atmospheric Ammonia: Detecting emission changes and environmental impacts*, 375-382. doi: 10.1007/978-1-4020-9121-6_22 Retrieved from https://doi.org/10.1007/978-1-4020-9121-6_22
- Cebula, J. (2009). Biogas purification by sorption techniques. *ACEE Journal*, 2, 95-103. Retrieved from http://delibra.bg.polsl.pl/Content/28143/BCPS_31742_-_Biogas-purification-_0000.pdf
- Chapin, F. S., Woodwell, G. M., Randerson, J. T., Rastetter, E. B., Lovett, G. M., Baldocchi, D. D., . . . Schulze, E. D. (2006). Reconciling Carbon-cycle Concepts, Terminology, and Methods. *Ecosystems*, 9(7), 1041-1050. doi: 10.1007/s10021-005-0105-7 Retrieved from <https://doi.org/10.1007/s10021-005-0105-7>
- Chowdhury, Z., Zain, S., Rashid, A., Rafique, R., & Khalid, K. (2012). Breakthrough curve analysis for column dynamics sorption of Mn (II) ions from wastewater by using Mangostana garcinia peel-based granular-activated carbon. *Journal of Chemistry*, 2013. doi: 10.1155/2013/959761 Retrieved from <http://dx.doi.org/10.1155/2013/959761>
- Chung, Y. C., Huang, C., Tseng, C. P., & Rushing Pan, J. (2000). Biotreatment of H₂S- and NH₃-containing waste gases by co-immobilized cells biofilter. *Chemosphere*, 41(3), 329-336. doi: 10.1016/S0045-6535(99)00490-7 Retrieved from [https://doi.org/10.1016/S0045-6535\(99\)00490-7](https://doi.org/10.1016/S0045-6535(99)00490-7)
- Chung, Y. C., Huang, C., & Tseng, C. P. (1996). Microbial oxidation of hydrogen sulfide with biofilter. *Journal of Environmental Science and Health. Part A: Environmental Science*

and Engineering and Toxicology, 31(6), 1263-1278. doi: 10.1080/10934529609376423
Retrieved from <https://doi.org/10.1080/10934529609376423>

Delhoménie, M. C., Bibeau, L., & Heitz, M. (2002). A study of the impact of particle size and adsorption phenomena in a compost-based biological filter. *Chemical Engineering Science*, 57(24), 4999-5010. doi: 10.1016/S0009-2509(02)00397-4 Retrieved from [https://doi.org/10.1016/S0009-2509\(02\)00397-4](https://doi.org/10.1016/S0009-2509(02)00397-4)

Delhoménie, M. C., & Heitz, M. (2005). Biofiltration of Air: A Review. *Critical Reviews in Biotechnology*, 25(1-2), 53-72. doi: 10.1080/07388550590935814 Retrieved from <https://doi.org/10.1080/07388550590935814>

Devinny, J. S., Deshusses, M. A., & Webster, T. S. (2017). *Biofiltration for air pollution control*: CRC press. Retrieved from <https://content.taylorfrancis.com/books/download?dac=C2006-0-16370-6&isbn=9781315138275&format=googlePreviewPdf>

Dillon, E. T. (1990). Composition and method for sweetening hydrocarbons: Google Patents.

Dumont, E. (2015). H₂S removal from biogas using bioreactors: a review. *International Journal of Energy and Environnement*, 6(5), 479-498. Retrieved from <https://hal.archives-ouvertes.fr/hal-01945143>

Elbert, W., Weber, B., Burrows, S., Steinkamp, J., Büdel, B., Andreae, M. O., & Pöschl, U. (2012). Contribution of cryptogamic covers to the global cycles of carbon and nitrogen. *Nature Geoscience*, 5, 459-462. doi: 10.1038/ngeo1486 Retrieved from <https://doi.org/10.1038/ngeo1486>

FAO. (2014). World reference base for soil resources 2014: international soil classification system for naming soils and creating legends for soil maps: FAO Rome, Italy.

Fernández-Delgado Juárez, M., Mostbauer, P., Knapp, A., Müller, W., Tertsch, S., Bockreis, A., & Insam, H. (2018). Biogas purification with biomass ash. *Waste Management*, 71, 224-232. doi: 10.1016/j.wasman.2017.09.043 Retrieved from <https://doi.org/10.1016/j.wasman.2017.09.043>

Field, C. B., Behrenfeld, M. J., Randerson, J. T., & Falkowski, P. (1998). Primary Production of the Biosphere: Integrating Terrestrial and Oceanic Components. *Science*, 281(5374),

237-240. doi: 10.1126/science.281.5374.237 Retrieved from <https://science.sciencemag.org/content/sci/281/5374/237.full.pdf>

- Gabriel, D., Cox, H., Brown, J., Torres, E., & Deshusses, M. (2002). Biotrickling filters for POTWs air treatment: Full-scale experience with a converted scrubber. *Proceedings of the Water Environment Federation, 2002*, 657-669. doi: 10.2175/193864702785140078
- Gosh, D. (2007). *Wet H₂S cracking problem in oil refinery processes—material selection and operation control issues*. Paper presented at the The 2007 Tri-Service Corrosion Conference.
- Goulden, M., & Crill, P. (1997). Automated measurements of CO₂ exchange at the moss surface of a black spruce forest. *Tree Physiology, 17*(8-9), 537-542.
- Groet, S. (1976). Regional and local variations in heavy metal concentrations of bryophytes in the northeastern United States. *Oikos, 445-456*.
- Hagen, M., Polman, E., Jensen, J. K., Myken, A., Joensson, O., & Dahl, A. (2001). Adding gas from biomass to the gas grid. *Contract No: XVII/4.1030(99-412)*.
- Hale, S., Hanley, K., Lehmann, J., Zimmerman, A., & Cornelissen, G. (2011). Effects of Chemical, Biological, and Physical Aging As Well As Soil Addition on the Sorption of Pyrene to Activated Carbon and Biochar. *Environmental Science & Technology, 45*(24), 10445-10453. doi: 10.1021/es202970x Retrieved from <https://doi.org/10.1021/es202970x>
- Hartikainen, T., Ruuskanen, J., Vanhatalo, M., & Martikainen, P. J. (1996). Removal of Ammonia from Air by a Peat Biofilter. *Environmental Technology, 17*(1), 45-53. doi: 10.1080/09593331708616359 Retrieved from <https://doi.org/10.1080/09593331708616359>
- Horikawa, M., Rossi, F., Gimenes, M., Costa, C., & Da Silva, M. (2004). Chemical absorption of H₂S for biogas purification. *Brazilian Journal of Chemical Engineering, 21*(3), 415-422.

- Iovane, P., Nanna, F., Ding, Y., Bikson, B., & Molino, A. (2014). Experimental test with polymeric membrane for the biogas purification from CO₂ and H₂S. *Fuel*, *135*, 352-358.
- Islamiyah, M., Soehartanto, T., Hantoro, R., & Abdurrahman, A. (2015). Water scrubbing for removal of CO₂ (carbon dioxide) and H₂S (hydrogen sulfide) in biogas from manure. *KnE Energy & Physics*, *2*(2), 126-131.
- Jensen, A. B., & Webb, C. (1995). Treatment of H₂S -containing gases: A review of microbiological alternatives. *Enzyme and Microbial Technology*, *17*(1), 2-10. doi: 10.1016/0141-0229(94)00080-B Retrieved from [https://doi.org/10.1016/0141-0229\(94\)00080-B](https://doi.org/10.1016/0141-0229(94)00080-B)
- Joshi, J. A., Hogan, J. A., Cowan, R. M., Strom, P. F., & Finstein, M. S. (2000). Biological Removal of Gaseous Ammonia in Biofilters: Space Travel and Earth-Based Applications. *Journal of the Air & Waste Management Association*, *50*(9), 1647-1654. doi: 10.1080/10473289.2000.10464189 Retrieved from <https://doi.org/10.1080/10473289.2000.10464189>
- Kandola, I., Pogrebnoi, A. M., & Pogrebnya, T. P. (2018). Oldoinyo Lengai volcanic ash for removal of hydrogen sulfide and ammonia from biogas. Retrieved from 10.4236/msce.2018.64010
- Kapdi, S., Vijay, V., Rajesh, S., & Prasad, R. (2005). Biogas scrubbing, compression and storage: perspective and prospectus in Indian context. *Renewable Energy*, *30*(8), 1195-1202.
- Kennes, C., & Veiga, M. C. (2004). Fungal biocatalysts in the biofiltration of VOC-polluted air. *Journal of Biotechnology*, *113*(1), 305-319. Retrieved from <https://doi.org/10.1016/j.jbiotec.2004.04.037>
- Kent, T. D., Williams, S. C., & Fitzpatrick, C. S. B. (2000). Ammoniacal Nitrogen Removal in Biological Aerated Filters: The Effect of Media Size. *Water and Environment Journal*, *14*(6), 409-414. doi: 10.1111/j.1747-6593.2000.tb00286.x Retrieved from <https://onlinelibrary.wiley.com/doi/abs/10.1111/j.1747-6593.2000.tb00286.x>

- Kim, J. H., Rene, E. R., & Park, H. S. (2008). Biological oxidation of hydrogen sulfide under steady and transient state conditions in an immobilized cell biofilter. *Bioresource Technology*, 99(3), 583-588. doi: 10.1016/j.biortech.2006.12.028 Retrieved from <https://doi.org/10.1016/j.biortech.2006.12.028>
- Kim, S., Kim, H. T., & Chi, B. (2004). Optimization of CO₂ absorption process with MEA solution. *Carbon Dioxide Utilization for Global Sustainability*, 153, 429-434.
- Ko, T. H. (2008). Removal of Hydrogen Sulfur from Coal-Derived Gas by Iron Oxides in Various Oxisols. *Environmental Engineering Science*, 25(7), 969-974. doi: 10.1089/ees.2007.0133 Retrieved from <https://doi.org/10.1089/ees.2007.0133>
- Ko, T. H. (2011). Application of Zn-contaminated soil: Feasibility study on the removal of H₂S from hot coal-derived gas. *Environmental Chemistry Letters*, 9(1), 77-82. doi: 10.1007/s10311-009-0249-3 Retrieved from <https://doi.org/10.1007/s10311-009-0249-3>
- Kohl, A. L., & Nielsen, R. (1997). *Gas Purification* (5th edition). Houston, Texas: Gulf Professional Publishing.
- Krich, K., Augenstein, D., Batmale, J., Benemann, J., Rutledge, B., & Salour, D. (2005). Biomethane from dairy waste. *A Sourcebook for the Production and Use of Renewable Natural Gas in California*, 147-162.
- Kuria, J., & Maringa, M. (2008). Developing simple procedures for selecting, sizing, scheduling of materials and costing of small bio-gas units. *International Journal for Service Learning in Engineering, Humanitarian Engineering and Social Entrepreneurship*, 3(1). doi: 10.24908/ijse.v3i1.2100 Retrieved from <https://doi.org/10.24908/ijse.v3i1.2100>
- Lal, R. (2009). Soil quality impacts of residue removal for bioethanol production. *Soil and Tillage Research*, 102(2), 233-241. doi: 10.1016/j.still.2008.07.003 Retrieved from <https://doi.org/10.1016/j.still.2008.07.003>
- Lasocki, J., Kołodziejczyk, K., & Matuszewska, A. (2015). Laboratory-scale investigation of biogas treatment by removal of hydrogen sulfide and carbon dioxide. *Polish Journal of Environmental Studies*, 24(3), 1427-1434.

- Lefèvre, C., Rekik, F., Alcantara, V., & Wiese, L. (2017). *Soil organic carbon: the hidden potential*. Rome, Italy: Food and Agriculture Organization of the United Nations (FAO). Retrieved from <http://www.fao.org/3/a-i6937e.pdf>
- Lehmann, J., & Joseph, S. (2015). *Biochar for environmental management: science, technology and implementation*: Routledge. Retrieved from <http://www.terrapreta.bioenergylists.org/files/A%20Future%20for%20Biochar%20in%20Vermont4.pdf>
- Lehmann, J., Kern, D., German, L., McCann, J., Martins, G. C., & Moreira, A. (2003). Soil Fertility and Production Potential. In J. Lehmann, D. C. Kern, B. Glaser & W. I. Wodos (Eds.), *Amazonian Dark Earths: Origin Properties Management* (pp. 105-124). Dordrecht: Springer Netherlands. Retrieved from https://doi.org/10.1007/1-4020-2597-1_6
- Lenhart, K., Weber, B., Elbert, W., Steinkamp, J., Clough, T., Crutzen, P., . . . Keppler, F. (2015). Nitrous oxide and methane emissions from cryptogamic covers. *Global Change Biology*, *21*(10), 3889-3900.
- Leson, G., Chavira, R., & Winer, A. (1995). *Experiences with a full-scale biofilter for control of ethanol emissions*. Paper presented at the A AND WMA ANNUAL MEETING.
- Leson, G., & Winer, A. M. (1991). Biofiltration: an innovative air pollution control technology for VOC emissions. *Journal of the Air & Waste Management Association*, *41*(8), 1045-1054.
- Li, Y., Wu, J., Shen, J., Liu, S., Wang, C., Chen, D., . . . Zhang, J. (2016). Soil microbial C:N ratio is a robust indicator of soil productivity for paddy fields. *Scientific Reports*, *6*, 35266. doi: 10.1038/srep35266 Retrieved from <https://doi.org/10.1038/srep35266>
- Liang, Y., Quan, X., Chen, J., Chung, J. S., Sung, J. Y., Chen, S., . . . Zhao, Y. (2000). Long-term results of ammonia removal and transformation by biofiltration. *Journal of Hazardous Materials*, *80*(1), 259-269. doi: 10.1016/S0304-3894(00)00314-9 Retrieved from [https://doi.org/10.1016/S0304-3894\(00\)00314-9](https://doi.org/10.1016/S0304-3894(00)00314-9)
- Lin, C. Y., Hesu, P. H., & Yang, D. H. (2001). Removal of Hydrogen Sulfide Gas and Landfill Leachate Treatment Using Coal Bottom Ash. *Journal of the Air & Waste Management*

Association, 51(6), 939-945. doi: 10.1080/10473289.2001.10464317 Retrieved from <https://doi.org/10.1080/10473289.2001.10464317>

Longdong, I. A., & Tooy, D. (2014). *Technical Study of a Downdraft Reactor In the Gasification Process of Coconut Husks*. Paper presented at the International Conference on Food, Agriculture and Biology (FAB-2014) Kuala Lumpur (Malaysia). <https://iicbe.org/upload/2617C614528.pdf>

López, M. E., Rene, E. R., Veiga, M. C., & Kennes, C. (2012). Biogas Technologies and Cleaning Techniques. In E. Lichtfouse, J. Schwarzbauer & D. Robert (Eds.), *Environmental Chemistry for a Sustainable World: Volume 2: Remediation of Air and Water Pollution* (pp. 347-377). Dordrecht: Springer Netherlands. Retrieved from https://doi.org/10.1007/978-94-007-2439-6_9

Loppi, S., & Bonini, I. (2000). Lichens and mosses as biomonitors of trace elements in areas with thermal springs and fumarole activity (Mt. Amiata, central Italy). *Chemosphere*, 41(9), 1333-1336.

Lorenz, K., Lal, R., Preston, C. M., & Nierop, K. G. J. (2007). Strengthening the soil organic carbon pool by increasing contributions from recalcitrant aliphatic bio(macro)molecules. *Geoderma*, 142(1), 1-10. doi: 10.1016/j.geoderma.2007.07.013 Retrieved from <https://doi.org/10.1016/j.geoderma.2007.07.013>

Mannucci, A., Munz, G., Mori, G., & Lubello, C. (2012). Biomass accumulation modelling in a highly loaded biotrickling filter for hydrogen sulphide removal. *Chemosphere*, 88(6), 712-717. doi: 10.1016/j.chemosphere.2012.04.026 Retrieved from <https://doi.org/10.1016/j.chemosphere.2012.04.026>

Manyà, J. J. (2012). Pyrolysis for Biochar Purposes: A Review to Establish Current Knowledge Gaps and Research Needs. *Environmental Science & Technology*, 46(15), 7939-7954. doi: 10.1021/es301029g Retrieved from <https://doi.org/10.1021/es301029g>

Mulat, D. G., Huerta, S. G., Kalyani, D., & Horn, S. J. (2018). Enhancing methane production from lignocellulosic biomass by combined steam-explosion pretreatment and bioaugmentation with cellulolytic bacterium *Caldicellulosiruptor bescii*. *Biotechnology for Biofuels*, 11(1), 19.

- Nash III, T. H., & Wirth, V. (1988). Lichens, bryophytes and air quality. *Bibliotheca Lichenologica*.
- Nelson, M., & Bohn, H. L. (2011). Soil-Based Biofiltration for Air Purification: Potentials for Environmental and Space LifeSupport Application. *Journal of Environmental Protection*, 2(08), 1084 - 1120.
- Nelson, M., Dempster, W., Alvarez-Romo, N., & MacCallum, T. (1994). Atmospheric dynamics and bioregenerative technologies in a soil-based ecological life support system: Initial results from biosphere 2. *Advances in Space Research*, 14(11), 417-426. doi: 10.1016/0273-1177(94)90331-X Retrieved from [https://doi.org/10.1016/0273-1177\(94\)90331-X](https://doi.org/10.1016/0273-1177(94)90331-X)
- Nortcliff, S., Hulpke, H., Bannick, C. G., Terytze, K., Knoop, G., Bredemeier, M., & Schulte-Bisping, H. (2000). Soil, 1. Definition, function, and utilization of soil. *Ullmann's Encyclopedia of Industrial Chemistry*.
- Perry, R. H., Green, D. W., & Maloney, J. O. (2008). *Perry's Chemical Engineers' Handbook* (8th ed.). New York: McGraw-Hill Retrieved from <https://b-ok.cc/ireader/1079007>
- Persson, M., Jönsson, O., & Wellinger, A. (2006). *Biogas upgrading to vehicle fuel standards and grid injection*. Paper presented at the IEA Bioenergy task.
- Petersson, A., & WellInGer, A. (2009). Biogas upgrading technologies—developments and innovations. *IEA Bioenergy*, 20, 1-19. Retrieved from https://www.iea-biogas.net/files/daten-redaktion/download/publi-task37/upgrading_rz_low_final.pdf
- Pham, C. H., Saggar, S., Berben, P., Palmada, T., & Ross, C. (2019). Removing Hydrogen Sulfide Contamination in Biogas Produced from Animal Wastes. *Journal of Environmental Quality*, 48, 32-38. doi: 10.2134/jeq2018.07.0271 Retrieved from <http://dx.doi.org/10.2134/jeq2018.07.0271>
- Primavera, A., Trovarelli, A., Andreussi, P., & Dolcetti, G. (1998). The effect of water in the low-temperature catalytic oxidation of hydrogen sulfide to sulfur over activated carbon. *Applied Catalysis A: General*, 173(2), 185-192. doi: 10.1016/S0926-860X(98)00178-1 Retrieved from [https://doi.org/10.1016/S0926-860X\(98\)00178-1](https://doi.org/10.1016/S0926-860X(98)00178-1)

- Qiu, Y., Zheng, Z., Zhou, Z., & Sheng, G. D. (2009). Effectiveness and mechanisms of dye adsorption on a straw-based biochar. *Bioresource Technology*, *100*(21), 5348-5351.
- Rasi, S., Veijanen, A., & Rintala, J. (2007). Trace compounds of biogas from different biogas production plants. *Energy*, *32*(8), 1375-1380. doi: 10.1016/j.energy.2006.10.018 Retrieved from <https://doi.org/10.1016/j.energy.2006.10.018>
- Rodriguez, J. A., Chaturvedi, S., Kuhn, M., & Hrbek, J. (1998). Reaction of H₂S and S₂ with Metal/Oxide Surfaces: Band-Gap Size and Chemical Reactivity. *The Journal of Physical Chemistry B*, *102*(28), 5511-5519. doi: 10.1021/jp9815208 Retrieved from <https://doi.org/10.1021/jp9815208>
- Rühling, Å. (1994). *Atmospheric Heavy Metal Deposition in Europe:—estimation based on moss analysis*: Nordic Council of Ministers.
- Ryckebosch, E., Drouillon, M., & Vervaeren, H. (2011). Techniques for transformation of biogas to biomethane. *Biomass and Bioenergy*, *35*(5), 1633-1645.
- Sahu, R. C., Patel, R., & Ray, B. C. (2011). Removal of hydrogen sulfide using red mud at ambient conditions. *Fuel Processing Technology*, *92*(8), 1587-1592. doi: <https://doi.org/10.1016/j.fuproc.2011.04.002> Retrieved from <http://www.science-direct.com/science/article/pii/S0378382011001238>
- Saini, B. (2010). *Introduction to Biotechnology* (Vol. 1): Laxmi Publications. <https://doi.org/10.1008/s13393-013-0120>
- Salum, A., & Hodes, G. S. (2009). *Leveraging CDM to scale-up sustainable biogas production from sisal waste*. Paper presented at the 17th European Biomass Conference and Exhibition: From Research to Industry and Markets.
- Sato, M. (1960). Oxidation of sulfide ore bodies. II. Oxidation mechanisms of sulfide minerals at 25 C. *Economic Geology and the Bulletin of the Society of Economic Geologists (US)*, *55*.
- Schulz, H., Dunst, G., & Glaser, B. (2013). Positive effects of composted biochar on plant growth and soil fertility. *Agronomy for Sustainable Development*, *33*(4), 817-827. doi:

10.1007/s13593-013-0150-0 Retrieved from <https://doi.org/10.1007/s13593-013-0150-0>

Sercu, B., Peixoto, J., Demeestere, K., van Elst, T., & Van Langenhove, H. (2006, 2006//). *Odors Treatment: Biological Technologies*. Paper presented at the Odors in the Food Industry, Boston, MA.

Sethupathi, S., Zhang, M., Rajapaksha, A. U., Lee, S. R., Mohamad Nor, N., Mohamed, A. R., . . . Ok, Y. S. (2017). Biochars as Potential Adsorbers of CH₄, CO₂ and H₂S. *Sustainability*, 9(1), 121. doi: 10.3390/su9010121 Retrieved from <https://www.mdpi.com/2071-1050/9/1/121>

Shackley, S., Carter, S., Knowles, T., Middelink, E., Haeefe, S., Sohi, S., . . . Haszeldine, S. (2012). Sustainable gasification–biochar systems? A case-study of rice-husk gasification in Cambodia, Part I: Context, chemical properties, environmental and health and safety issues. *Energy Policy*, 42, 49-58. doi: <https://doi.org/10.1016/j.enpol.2011.11.026> Retrieved from <http://www.sciencedirect.com/science/article/pii/S0301421511009037>

Shareefdeen, Z. (2005). *Biotechnology for odor and air pollution control*. Heidelberg, Germany: Springer Science & Business Media. Retrieved from <https://b-ok.cc/ireader/2095298>

Singh, R., & Mandal, S. K. (2011). Microbial Removal of Hydrogen Sulfide from Biogas. *Energy Sources, Part A: Recovery, Utilization, and Environmental Effects*, 34(4), 306-315. doi: 10.1080/15567030903330686 Retrieved from <https://doi.org/10.1080/15567030903330686>

Skerman, A. G., Heubeck, S., Batstone, D. J., & Tait, S. (2017). Low-cost filter media for removal of hydrogen sulphide from piggery biogas. *Process Safety and Environmental Protection*, 105, 117-126. doi: 10.1016/j.psep.2016.11.001 Retrieved from <https://doi.org/10.1016/j.psep.2016.11.001>

Smith, J., Lipsitch, M., & Almond, J. W. (2011). Vaccine production, distribution, access, and uptake. *The Lancet*, 378(9789), 428-438.

- Sorial, G. A., Smith, F. L., Suidan, M. T., Biswas, P., & Brenner, R. C. (1997). Performance of peat biofilter: impact of the empty bed residence time, temperature and toluene loading. *Journal of Hazardous Materials*, 53(1), 19-33. doi: 10.1016/S0304-3894(96)01842-0 Retrieved from [https://doi.org/10.1016/S0304-3894\(96\)01842-0](https://doi.org/10.1016/S0304-3894(96)01842-0)
- Steffen, R., Szolar, O., & Braun, R. (1998). Feedstocks for anaerobic digestion. *Institute of Agrobiotechnology Tulin, University of Agricultural Sciences, Vienna*.
- Surda, P., & Vitkova, J. (2016). Impact of biochar application on soil moisture dynamics and saturated hydraulic conductivity. *International Multidisciplinary Scientific GeoConference: SGEM: Surveying Geology & Mining Ecology Management, 1*, 445-451.
- Syed, M., Soreanu, G., Falletta, P., & Béland, M. (2006). Removal of hydrogen sulfide from gas streams using biological processes. A review. *Canadian Biosystems Engineering*, 48, 2.
- Thrän, D., Billig, E., Persson, T., Svensson, M., Daniel-Gromke, J., Ponitka, J., & Seiffert, M. (2014). *Biomethane: Status and Factors Affecting Market Development and Trade: a Joint Study*: IEA Bioenergy. Retrieved from <http://task40.ieabioenergy.com/wp-content/uploads/2013/09/t40-t37-biomethane-2014.pdf>
- Tippayawong, N., & Thanompongchart, P. (2010). Biogas quality upgrade by simultaneous removal of CO₂ and H₂S in a packed column reactor. *Energy*, 35(12), 4531-4535. doi: 10.1016/j.energy.2010.04.014 Retrieved from <https://doi.org/10.1016/j.energy.2010.04.014>
- Tseng, T. K., Chang, H. C., Chu, H., & Chen, H. T. (2008). Hydrogen sulfide removal from coal gas by the metal-ferrite sorbents made from the heavy metal wastewater sludge. *Journal of Hazardous Materials*, 160(2), 482-488. doi: 10.1016/j.jhazmat.2008.03.058 Retrieved from <https://doi.org/10.1016/j.jhazmat.2008.03.058>
- Turetsky, M. R. (2003). The Role of Bryophytes in Carbon and Nitrogen Cycling. *The Bryologist*, 106(3), 395-409, 315. doi: <https://doi.org/10.1639/05> Retrieved from <http://www.bioone.org/doi/full/10.1639/05>

- Van Zwieten, L., Kimber, S., Morris, S., Chan, K. Y., Downie, A., Rust, J., . . . Cowie, A. (2010). Effects of biochar from slow pyrolysis of papermill waste on agronomic performance and soil fertility. *Plant and Soil*, 327(1), 235-246. doi: 10.1007/s11104-009-0050-x Retrieved from <https://doi.org/10.1007/s11104-009-0050-x>
- Vannini, C., Munz, G., Mori, G., Lubello, C., Verni, F., & Petroni, G. (2008). Sulphide oxidation to elemental sulphur in a membrane bioreactor: Performance and characterization of the selected microbial sulphur-oxidizing community. *Systematic and Applied Microbiology*, 31(6), 461-473. doi: 10.1016/j.syapm.2008.07.003 Retrieved from <https://doi.org/10.1016/j.syapm.2008.07.003>
- Vlasceanu, L., Popa, R., & Kinkle, B. K. (1997). Characterization of *Thiobacillus thioparus* LV43 and its distribution in a chemoautotrophically based groundwater ecosystem. *Applied and Environmental Microbiology*, 63(8), 3123. Retrieved from <http://aem.asm.org/content/63/8/3123.abstract>
- Wani, A. H., Lau, A. K., & Branion, R. M. R. (1999). Biofiltration control of pulping odors – hydrogen sulfide: performance, macrokinetics and coexistence effects of organo-sulfur species. *Journal of Chemical Technology & Biotechnology*, 74(1), 9-16. doi: 10.1002/(SICI)1097-4660(199901)74:1<9::AID-JCTB981>3.0.CO;2-B Retrieved from [https://doi.org/10.1002/\(SICI\)1097-4660\(199901\)74:1<9::AID-JCTB981>3.0.CO;2-B](https://doi.org/10.1002/(SICI)1097-4660(199901)74:1<9::AID-JCTB981>3.0.CO;2-B)
- Weast, R. C., Astle, M., & Beyer, W. (1984). *Handbook of Chemistry and Physics* (64th ed.). Boca Raton, Florida: CRC Press, Inc.
- Weiland, P. (2010). Biogas production: current state and perspectives. *Appl Microbiol Biotechnol*, 85(4), 849-860. doi: 10.1007/s00253-009-2246-7
- Winner, W. (1988). Responses of bryophytes to air pollution. *Lichens, Bryophytes and Air Quality*. Cramer, Berlin, 141-173.
- Wolverton, B. C., McDonald, R. C., & Watkins, E. A. (1984). Foliage plants for removing indoor air pollutants from energy-efficient homes. *Economic Botany*, 38(2), 224-228. doi: 10.1007/bf02858837 Retrieved from <https://doi.org/10.1007/BF02858837>

- Wrb, I. W. G. (2015). World reference base for soil resources 2014, update 2015: International soil classification system for naming soils and creating legends for soil maps. *World Soil Resources Reports No. 106*, 192.
- Xie, M., Leung, A. K., & Ng, C. W. W. (2017). Mechanisms of hydrogen sulfide removal by ground granulated blast furnace slag amended soil. *Chemosphere*, *175*, 425-430. doi: 10.1016/j.chemosphere.2017.02.016 Retrieved from <https://doi.org/10.1016/j.chemosphere.2017.02.016>
- Yang, Y., & Allen, E. R. (1994). Biofiltration Control of Hydrogen Sulfide 1. Design and Operational Parameters. *Air & Waste*, *44*(7), 863-868. doi: 10.1080/1073161X.1994.10467287 Retrieved from <https://doi.org/10.1080/1073161X.1994.10467287>
- Yoon, I. K., & Park, C. H. (2002). Effects of gas flow rate, inlet concentration and temperature on biofiltration of volatile organic compounds in a peat-packed biofilter. *Journal of Bioscience and Bioengineering*, *93*(2), 165-169. doi: 10.1016/S1389-1723(02)80009-3 Retrieved from [https://doi.org/10.1016/S1389-1723\(02\)80009-3](https://doi.org/10.1016/S1389-1723(02)80009-3)
- Zhao, Q., Leonhardt, E., MacConnell, C., Frear, C., & Chen, S. (2010). Purification technologies for biogas generated by anaerobic digestion. *Compressed Biomethane, CSANR, Ed.* Retrieved from www.build-a-biogas-plant.com/PDF/BiogasPurificationTech2010.pdf
- Zicari, S. M. (2003). *Removal of hydrogen sulfide from biogas using cow-manure compost.* Cornell University. Retrieved from [https://www.wellowgate.co.uk/biogas/H2S_removal .pdf](https://www.wellowgate.co.uk/biogas/H2S_removal.pdf)

APPENDICES

Appendix 1: The soil samples and Profile Statistics collected from Tanzania Agricultural Research Institute (TARI) located in Tanga

	Location	Sample	Depth	Physical Properties
	KGR P/5	A1	0-15/20 cm	Dark red 2.5 YR 3/6 dry, 2.5 YR 2.5/4 dark reddish brown moist; clay, slightly hard dry, friable moist and sticky
<p>World Reference Base for Soil Resources WRB (FAO, 2014): Lixic Rhodic Ferralsol (Clayic, Cutanic, Profondic)</p>				
	KGR P/6	Ap	0-20/25 cm	Black 10 YR 2/1 moist; clay loam, friable moist, sticky and plastic wet; moderate fine and medium sub-angular blocks.
<p>World Reference Base for Soil Resources WRB (FAO, 2014): Endocalcaric Stagnic Luvisol (Eutric, Humic, Profondic)</p>				
		Btg1	20/25-40 cm	Very dark greyish brown 10 YR 3/2 moist; clay, very firm moist, sticky and plastic wet;

Location	Sample	Depth	Physical Properties
			moderate medium and coarse angular blocks;
KGR P/6	Ap	0- 20/25 cm	Black 10 YR 2/1 moist; clay loam, friable moist, sticky and plastic wet; moderate fine and medium sub-angular blocks; many fine and very fine pores; common fine and very fine roots;
	Btg1	20/25- 40 cm	Very dark greyish brown 10 YR 3/2 moist; clay, very firm moist, sticky and plastic wet; moderate medium and coarse angular blocks; patchy thin clay cutans; brown



World Reference Base for Soil Resources WRB
(FAO, 2014): Rhodic Lixisol (Clayic, Cutanic
Profondic)

Appendix 2: Mass composition of soil in the Filters

Soil type	Filter type	Weight of empty container (g)	Weight of aerator and small gravels	Weight of soil sample (g)	Weight of charcoal dust (g)	Weight of gravel packs (g)	Weight of moss substrate (g)	Total weight of the filter (g)
	1	100	200	100	100	1200	545	2245
T1, T2,	2	100	200	150	100	1200	545	2295
T3 and T4	3	100	200	100	100	1200	545	2345

Appendix 3: On site setup of the experiment

